



Cite this: *Chem. Commun.*, 2023, 59, 1554

Recent developments in visible light induced polymerization towards its application to nanopores

Claire Förster and Annette Andrieu-Brunsen *

Visible light induced polymerizations are a strongly emerging field in recent years. Besides the often mild reaction conditions, visible light offers advantages of spatial and temporal control over chain growth, which makes visible light ideal for functionalization of surfaces and more specifically of nanoscale pores. Current challenges in nanopore functionalization include, in particular, local and highly controlled polymer functionalizations. Using spatially limited light sources such as lasers or near field modes for light-induced polymer functionalization is envisioned to allow local functionalization of nanopores and thereby improve nanoporous material performance. These light sources are usually providing visible light while classical photopolymerizations are mostly based on UV-irradiation. In this review, we highlight developments in visible light induced polymerizations and especially in visible light induced controlled polymerizations as well as their potential for nanopore functionalization. Existing examples of visible light induced polymerizations in nanopores are emphasized.

Received 3rd December 2022,
Accepted 13th January 2023

DOI: 10.1039/d2cc06595a

rsc.li/chemcomm

Macromolecular Chemistry – Smart Membranes, Technische Universität Darmstadt, 64287, Darmstadt, Germany. E-mail: annette.andrieu-brunsen@tu-darmstadt.de



Claire Förster

local nanopore functionalization and polymer writing.

Claire Förster studied Chemistry at the Technical University of Darmstadt (Germany) and received her BSc degree in 2017 and her MSc degree in 2019. During her Master Thesis she worked on pH-reporter dyes and pH-detection in confined space of nanopores. She is currently pursuing her PhD degree under the supervision of Prof. Andrieu-Brunsen. Her main scientific interests are focused on visible light induced polymerizations for



Annette Andrieu-Brunsen

Professor at the TU-Darmstadt (Germany). In 2018 she was appointed as an associate professor at TU-Darmstadt and in 2020 she was appointed as a full professor at TU Darmstadt (Germany). She received several awards and was granted an ERC StG in 2018. Her research interest focuses on functional nanopore and nanopore transport design. This includes polymer functionalization of spatially confined nanopores, nanopore wetting and charge control, innovative nanoporous material and architecture design as well as automated design procedures.

Annette Andrieu-Brunsen studied Chemistry at the Philipps Universität Marburg (Germany). She got her PhD from the Johannes-Gutenberg Universität and the Max-Planck-Institute for Polymer Research in Mainz (Germany) partly funded by the Studienstiftung des Deutschen Volkes in 2010 and has been working together with Prof. Soler-Illia and Prof. Azzaroni at the CNEA in Buenos Aires (Argentina) before being appointed as the Assistant



Introduction

Polymer functionalization of nanoscale pores advanced in the last years. This advance has been driven by the resulting material properties but as well by new possibilities in the field of polymerization itself, as *e.g.* the increasing number of reported visible light induced polymerizations.^{1–3} Polymer functionalized nanopores, for example, allow for specific control of molecular transport which is relevant in separation, energy conversion, sensing, or release.^{2,4–10} Especially, gating of molecular transport using stimuli-responsive polymers in nanopores has been demonstrated for all possible stimuli from pH, ion interaction to redox or even magnetic gating.^{7,11} However, for nanopore transport beyond gating, controlled- and local (polymer-) functionalization is one essential tool aiming to control polymer amount, chain composition, and local gradient formation for various monomers. Such asymmetric design of porous materials has been shown to result in Janus materials for side selective separation or increased transport performance.^{3,12} For example, theoretical studies from Huang and Szeleifer demonstrated the relevance of controlled and local nanopore functionalization, as well as polymer sequence design of nanopores allowing transport direction.^{13,14}

An experimental implementation of local polymer functionalization including polymer sequence design has to be based on controlled (living) polymerizations. The general concept of controlled (living) polymerizations was first realized for anionic polymerizations in 1956.¹⁵ A more robust way to control polymer functionalization tolerating a large variety of different monomers can be realized by controlled radical polymerizations. Often-used controlled radical polymerizations are atom transfer radical polymerization (ATRP),^{16,17} reversible addition fragmentation chain transfer polymerization (RAFT),¹⁸ nitroxide-mediated radical polymerization^{19,20} (NMP) and iniferter initiated polymerization.^{21–23} In recent years these polymerizations were increasingly often initiated using visible light irradiation including spatial and temporal control over chain growth for example at planar surfaces. Furthermore, these polymerizations allow for mild reaction conditions, since the use of light often eliminates the need for high temperatures.²⁴

Although, most polymerization initiators absorb UV-light, visible light, here defined for wavelength between 380–750 nm, is an interesting trigger. Among others, it is cheap, abundant in nature, and lasers usually operate in the visible wavelength range.²⁵ Furthermore, initiation by visible light is often considered to be sustainable as it allows to use sunlight and bears some aspects of green chemistry as it is abundant in nature.^{26–28} Thereby, both, catalyst-free approaches and polymerization with the use of photo catalysts were realized, to date.^{29–31}

Besides visible light irradiation, also high throughput processes are an emerging field of research, in context of polymer synthesis.^{32–35} In particular visible light can be used for realization of high throughput processes.^{33,36,37} Data driven material design needs large data and sample sets as shown for data driven nanopore application in the context of sensing.^{3,38} Thus, automated synthesis is essential and of potentially increasing

importance in future. This renders visible light induced polymerization with a potential for automated process design interesting.

In this review different visible light induced polymerization techniques are discussed in more detail, focusing on their potential for nanopore functionalization and especially for (nano)local and automated polymer nanopore functionalization. In addition, especially examples for visible light induced polymerizations in nanopores are highlighted.

Free radical polymerizations initiated by visible light

Visible light induced free radical polymerizations receive increasing attention within the last decade. In general, two classes of photoinitiators are used for visible light induced, free radical polymerizations: Type I photoinitiators generate radicals by irradiation to a single-molecule bond cleavage. Type II photoinitiators generate radicals by interaction with a second molecule due to a bimolecular reaction after irradiation.^{39,40} For visible light irradiation mostly type II photoinitiators are used.³⁹

But especially in the last decade also type I photoinitiators were developed for visible light induced polymerizations.⁴¹ For example He *et al.*⁴² recently used the type I photoinitiator dimethyl 1,4-dibenzoylformate (DM-BD-F) under 405 nm irradiation to polymerize acrylate monomers. But also wavelength up to 600 nm were used for visible light induced polymerizations initiated by type I photoinitiators, as demonstrated by the group of Haas using triacylstannenolates as initiator.⁴³ Currently, especially the broadening of the applicable wavelengths range, water solubility, automated fabrication technology as well as absorption and bleaching behaviour of type I photoinitiators for visible light induced polymerizations are investigated.⁴¹ In the following two aspects are highlighted in more detail: dye-sensitized polymerizations which allow to use a broad wavelength range as well as to polymerize in water and the application of visible-light induced free radical polymerizations for additive manufacturing as automated fabrication method.

With respect to broadening the wavelength range and allowing polymerization in water an interesting free radical visible light induced polymerization, based on type II photoinitiators, is the so-called dye-sensitized photopolymerization. Dye-sensitized polymerizations allow polymerization at basically the entire visible light wavelength range depending on the selected dye photosensitizer absorption. Lalev e and Fouassier summarized trends in dye sensitized radical polymerizations in their book “Dyes and Chromophores in Polymer Science” (2015).⁴⁴ Briefly, by using two-component photo initiating systems (Fig. 1a),⁴⁵ consisting of a photosensitizer (dye) and a coinitiator (*e.g.* a tertiary amine) polymerizations using various dyes and thus at different wavelengths are accessible.⁴⁶ For example cyanine dyes together with irradiation at a wavelength range of 510–570 nm⁴⁷ were addressed. While using methylene blue red light with a



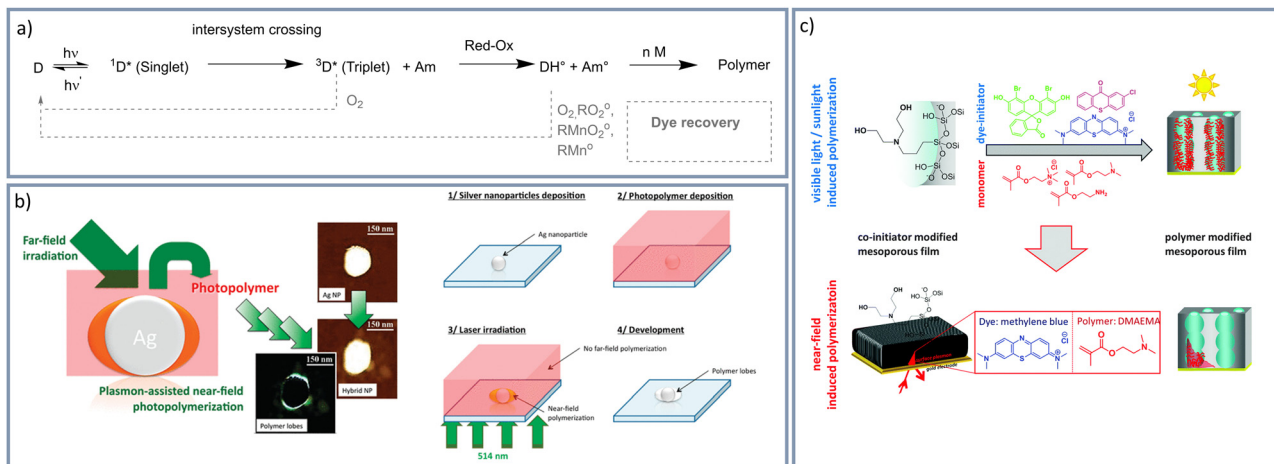


Fig. 1 (a) Photopolymerization by dye (d)-amine (Am)-System.⁴⁵ Adapted with permission from *J. Am. Chem. Soc.*, 2011, **133**, 10535–10542.⁴⁵ Copyright 2021 American Chemical Society. (b) Plasmon-assisted near field photopolymerization by Deeb *et al.*⁴⁵ Reprinted (adapted) with permission from *J. Am. Chem. Soc.*, 2011, **133**, 10535–10542.⁴⁵ Copyright 2021 American Chemical Society. (c) Plasmon near-field induced surface polymer modification of mesoporous thin silica films.⁴⁸ Reprinted with permission *Chem. Commun.*, 2015, **51**, 11697–11700.⁴⁸ Copyright 2015 Royal Society of Chemistry.

wavelength around 660 nm was used to initiate this radical polymerization.⁴⁸ But also sunlight was used for polymerization using various dyes.⁴⁹ Deeb *et al.*⁴⁵ performed a nanoscale dye-sensitized visible-light induced photopolymerization using surface plasmons generated by silver nanoparticles (Fig. 1b). They show nanoscale polymer formation in the areas of surface plasmon enhancement by selecting an irradiation energy below a so-called threshold energy. In further work, it was demonstrated that polymerization is indeed initiated *via* the photochemical mechanism and not by local temperature increase or hot electrons under the applied low irradiation energy.⁵⁰ Our research group^{48,51,52} applied dye-sensitized visible-light induced photopolymerizations using a dye-tertiary amine photosensitizer, photoinitiator combination for mesoporous silica functionalization resulting in polymer-dominated gating of ionic mesopore accessibility. By using surface plasmons localized polymer functionalization in mesoporous layers was achieved (Fig. 1c).⁴⁸ Besides using visible light and implementing local control on polymer placement, automation of polymerization is of relevance especially in data-driven material design approaches which need large data sets. Automation of local polymer structuring using visible light induced free radical polymerizations was realized using direct laser writing (DLW) in combination with photoresists. This combination led to the development of additive manufacturing of three dimensional polymer materials.^{53–55} The combination of visible light induced, free radical polymerization with 3D printing is a rapidly growing research area.^{41,56,57} For example, Lalev e and colleagues⁵⁸ used ketone derivatives for a free radical polymerization under 405 nm light and demonstrated 3D printing. Breloy *et al.*⁴⁶ used methacrylated quinizarin derivatives to achieve complex 3D biosourced structures under 405 nm light irradiation for 3D-photoprinting technology. Also using 405 nm, Zhao and colleagues⁵⁹ used dealkaline lignin for digital light processing 3D printing. Zhang *et al.*⁶⁰ used blue, green, yellow, and red LEDs to initiate a free radical polymerization and furthermore, demonstrated 3D printing by using a polychromatic

visible light (400–730 nm) 3D printer. In nanoporous materials DLW or 3D printing in combination with free radical polymerizations have not been demonstrated to date.

Visible light induced ATRP

Besides, the above mentioned free radical polymerization ATRP, as one of the most widely used methods of controlled radical polymerization,^{16,61} was applied to surface polymer grafting using porous silica in 1997 by Huang and Wirth.⁶² In 2012 Kruk⁶³ summarized polymer functionalization of mesoporous silica using ATRP. For example, Fu *et al.*⁶⁴ reported the adjustment of pore sizes in mesoporous silica particles due to increasing polymer amount using ATRP. The group of Sch onherr⁶⁵ recently analyzed the confinement effects in anodic alumina nanopores and demonstrated the effect of curvature and pore diameter effect on the polymerization kinetics using SI-ATRP. ATRP was as well used to functionalize mesoporous silica^{66–70} and ion track etched pores^{71–73} with different polyelectrolytes to study *e.g.* the resulting permselective ion transport in such polyelectrolyte functionalized mesoporous thin films. In the last years research has been directed, among others, towards visible light induced ATRP. The majority of studies focuses on solution polymerization. Thereby often small amounts of metal catalysts have been used. But also metal-free visible light induced ATRPs based entirely on organic catalysts have been reported. Since 2014 photoinduced organocatalyzed ATRP gained increasing interest.⁷⁴ Konkolewicz *et al.*⁷⁵ used a few ppm of copper catalyst for a photoinduced ATRP under blue and violet LED irradiation and even sunlight whereby at 631 nm no successful ATRP was observed. Also in the presence of ppm copper catalysts Ciftci *et al.*⁷⁶ managed a visible light induced ATRP using $\text{Mn}_2(\text{CO})_{10}$ as photocatalyst. Pan *et al.*⁷⁷ described an ATRP, which was induced at 392 nm. Upon 380 nm irradiation, a controlled radical polymerization



Highlight

using $\text{Ir}(\text{ppy})_3$ (ppy = 2-pyridylphenyl) as photoredox catalyst was reported by Treat *et al.*⁷⁸ Because of the robust nature of the catalyst the polymerization allows even monomers with acid groups to be polymerized. $\text{Ir}(\text{ppy})_3$ as photoredox catalyst was as well applied by the group of Zhu⁷⁹ performing a visible light induced ATRP. Zhu *et al.* managed to separate and recycle the catalyst after polymerization. Besides metal organic complexes, organic photocatalysts were used for visible light induced ATRPs. Matyjaszewski and coworkers⁸⁰ reported a green light induced ATRP using a combination of Eosin Y and a copper catalyst to achieve ATRP in contact with air. In 2014 visible light induced, metal free ATRPs were reported by the groups of Hawker⁸¹ and Theriot.⁸² But already in 2012 the group of Yagci⁸³ described the control of molecular weight and distribution using bis (2,4,6-trimethylbenzoyl) phenylphosphine oxide (BAPO), Eosin Y, and Erythrosin B at 400–500 nm light for ATRP. Liu *et al.*⁸⁴ used fluorescein as organocatalyst, the group of Yagci⁸⁵ used reducible dyes and amine as well as alkylhalides, and Wang *et al.*⁸⁶ described an ATRP with an organic semiconductor based visible light activated photo catalyst. In 2018 Xu *et al.*⁸⁷ demonstrated the suitability of metal-free, visible light induced ATRP for the polymerization of acrylamides. Very recently Qiao *et al.*⁸⁸ used carbon quantum dots as catalyst for a visible light induced ATRP at 405 nm. Using these carbon quantum dots a high monomer conversion of more than 90% in one minute was achieved, making polymerization suitable for 3D printing.⁸⁸ Although most of the visible light induced ATRP

were performed at wavelengths below 600 nm, there have been studies on ATRP using 630 nm⁸⁹ or even using near infrared irradiation.⁹⁰

These initial developments on visible light induced ATRP in solution were also transferred to surface grafting of polymers using visible light induced ATRPs. Bansal *et al.*⁹¹ reported a surface initiated ATRP (SI-ATRP) under visible light irradiation using tetrasulfonated copper(II) phthalocyanine (CuPcS) as catalyst (Fig. 2a). Under visible light irradiation CuPcS is reduced to Cu(I) complex by a one-electron transfer process.⁹¹ To achieve polymer grafting in a first step Bansal *et al.*⁹¹ functionalized TiO_2 -particles with (3-aminopropyl)triethoxysilane and 2-bromoisobutyl bromide, which was used as initiator for the surface initiated polymerization. The polymerization was then carried out using visible light irradiation and a varying irradiation time of 5–24 h at room temperature. Also on surfaces Jiang *et al.* prepared self-healing nanocomposite hydrogels using a SI-PET (photoinduced electron/energy transfer)-ATRP under visible light irradiation for 15 h.⁹² Fan *et al.*⁹³ also performed a SI-PET-ATRP to prepare self-healing nanocomposite hydrogels. As in solution, on surfaces metal free ATRPs are carried out in recent years. The group of Hawker⁹⁴ reported a metal free SI-ATRP under visible light at 405 nm and room temperature. They used *N*-phenyl phenothiazine (PTH) as catalyst and an irradiation time from 0.5–4 h. The group of Matyjaszewski⁹⁵ used PTH as photocatalyst while functionalizing 16 nm and 120 nm silica nanoparticles with poly(methyl methacrylate)

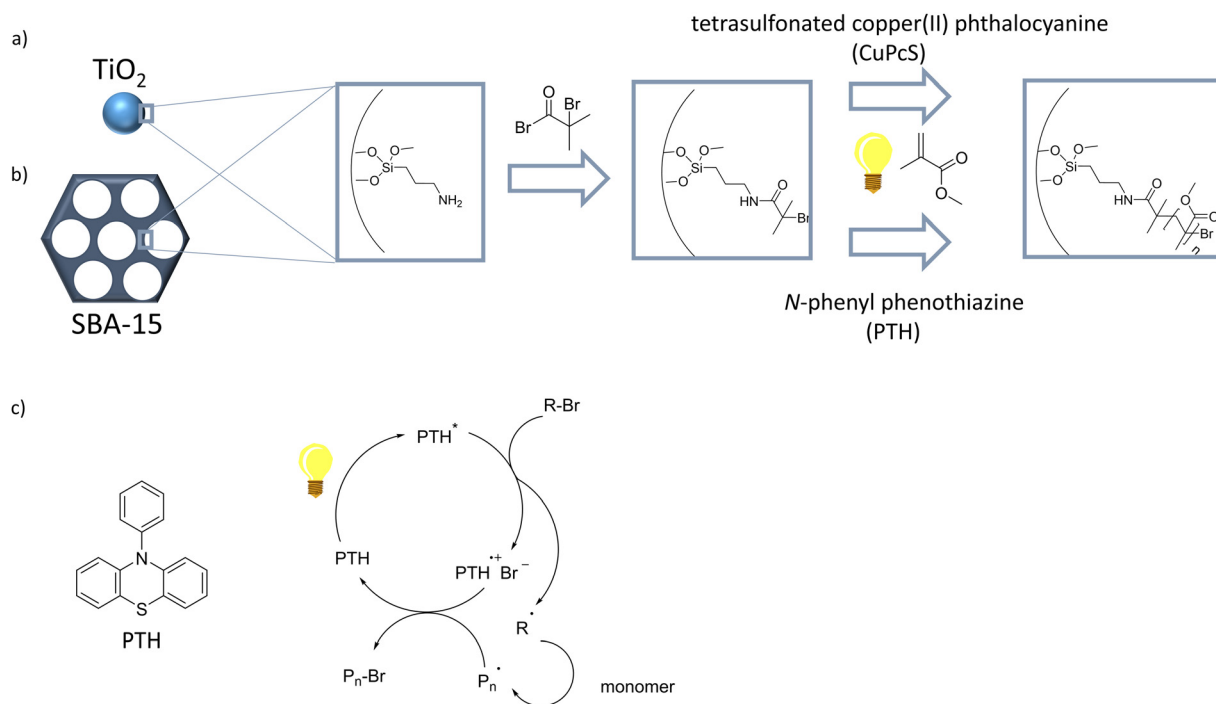


Fig. 2 (a) SI-ATRP under visible light irradiation on TiO_2 particles using CuPcS as photo catalyst by Bansal *et al.*⁹¹ Adapted with the permission from *RSC Adv.*, 2015, **5**, 21189–21196.⁹¹ Copyright 2015 Royal society of chemistry. (b) SI-ATRP under visible light irradiation on SBA-15 using PTH as photo catalyst by Ma *et al.*⁹⁸ Adapted with permission from *Polymers*, 2017, **9**, 58.⁹⁸ Copyright 2017 by the authors; licensee MDPI, Basel, Switzerland. (c) Mechanism of the metal free photo initiated ATRP using PTH as photo catalyst by the group of Yagci.⁹⁹ Reprinted with the permission from *Polym. Chem.*, 2016, **7**, 6039–6043.⁹⁹ Copyright 2016 Royal society of chemistry.



using a wavelength of 365 nm. Also using irradiation of 365 nm and PTH as catalyst SI-ATRP's to functionalize mesoporous silica polymer nanocomposites⁹⁶ and SBA-15⁹⁷ were reported. A visible light induced SI-ATRP in mesoporous silica was as well achieved by Ma *et al.*⁹⁸ while using 380 nm light to functionalize SBA-15 (Fig. 2b). The group of Yagci⁹⁹ analyzed the photo-initiation mechanism of photoinduced metal free ATRP using PTH (Fig. 2c).

Also performing a metal-free SI-ATRP on SBA-15 the group of Zhang^{100,101} used fluorescein as photo catalyst and triethylamine as electron donor under blue light irradiation. Another example of pore functionalization using visible light induced ATRP was performed by Meng *et al.*,¹⁰² while using the photo catalyst *fac*-[Ir(ppy)₃] they functionalized microporous polypropylene membrane (MPPM) surfaces with methacrylates and diblock copolymer brushes. Local polymer-reinitiation at the nanoscale has recently been demonstrated by Soppera and Colleagues¹⁰³ using a visible light induced ATRP and surface plasmons at 532 nm.

Numerous visible light induced ATRP's have been performed at different wavelengths, both with and without metal catalysts. The listed examples clearly show that visible light induced ATRP is well studied in solution, and that it is increasingly studied on surfaces, while it becomes recently a research topic also in porous materials.

Visible light induced RAFT and Iniferter initiated polymerizations

Besides ATRP, RAFT is a versatile controlled radical polymerization mechanism as well applied to porous materials and in recent years combined with visible light irradiation. The classical RAFT polymerization was reported in 1988 by the Commonwealth Scientific and Industrial Research Organization (CSIRO) research group.¹⁸ One advantage of RAFT polymerization is the large variety of different monomers which are compatible with the RAFT mechanism. Because of the high tolerance to different functional groups the polymerization can even be performed in aqueous solution. The RAFT process uses thiocarbonylthio-compounds to control the polymerization. Basis of the polymerization is the reversible degenerative chain transfer.¹⁰⁴ The mechanism of RAFT consists mainly of two reactions: the pre-equilibrium and the main equilibrium.

RAFT agents show characteristic colors, which indicate their absorbance in the visible light region such as the yellow trithiocarbonates and dithiobenzoates being red. When the RAFT agents are exposed to suitable light, carbon-centered and sulfur-centered radicals are generated. The carbon-centered radicals are usually responsible for initiating the polymerization.¹⁰⁵ The photolytic stability of various RAFT agents under blue light was analyzed by the group of Qiao.¹⁰⁶ They reported that the stability of the RAFT agent (*i.e.* thiocarbonylthio-compounds) depends on the structure of the fragmenting group (*R*-). The reactivity of the carbon-centered radical depends on the photolytic cleavage.¹⁰⁶

Light induced RAFT is usually realized either by the PET¹⁰⁷ or the iniferter (initiator-transferagent-terminator²¹) approach.¹⁰⁸ Thereby, PET-RAFT is a visible light induced variant of the RAFT polymerization, which was developed in 2014 by the group of Boyer.¹⁰⁷ Interestingly, this PET-RAFT provides oxygen tolerance under ambient conditions and can be performed either using a transition metal-based or an organic photoredox catalyst such as *e.g.* Ru(bpy)₃Cl₂, ZnTPP or Eosin Y, respectively.¹⁰⁹ The alternative approach of iniferter initiated polymerization using RAFT agents to polymerize upon visible light irradiation were first investigated by Otsu.¹¹⁰ Already in 1958 Otsu and Nayatani¹¹¹ used thiuram disulfides to polymerize styrol in solution discussing two types of iniferters: an asymmetric A-B type and a symmetric C-C type iniferter,^{110,112} where the A-B type is preferred for better reactivity control, and *e.g.* preparation of block-*co*-polymers.¹¹⁰ For further details on iniferter initiated polymerizations we recommend the article by Otsu.¹¹⁰

As already observed for ATRP a significant number of visible light induced RAFT and iniferter initiated polymerizations were performed in solution and on planar surfaces. Especially the relatively recently reported PET-RAFT seems to be promising for controlled visible light induced polymer functionalization. Depending on the required wavelength, different catalysts can be used, both on metal and organic basis. In comparison to PET-RAFT polymerization, which can be initiated up to 850 nm,¹¹³ iniferter initiated polymerizations are usually initiated at a wavelength below 400 nm. Whereas, in recent years iniferter initiated polymerizations using visible light were also described. On the other hand, iniferter initiated polymerization don't require any additional photo catalyst, which might be advantageous in the context of nanopore polymer functionalization with respect to reagent availability in these nanopores during polymerization.

In 2014 visible light induced PET-RAFT using Ir(ppy)₃ as photocatalyst was reported.¹⁰⁷ Since then zinc tetraphenylporphyrin (ZnTPP) was frequently used as metal-based photo catalyst in visible light induced PET-RAFT.^{36,114-118} Very recently Wanasinghe *et al.*¹¹⁶ used both Ir(ppy)₃ and ZnTPP to analyze bulk swelling ratios and homogeneity of polymer networks, whereby better results were reported using ZnTPP. Corrigan *et al.*¹¹⁹ used ZnTPP as photoredox catalyst for a PET-RAFT polymerization at low-intensity yellow light irradiation, ambient temperatures, and in an open reaction vessel in the presence of oxygen. Also by using ZnTPP Shanmugam *et al.*¹²⁰ polymerized styrene, (meth)acrylates, and (meth)acrylamides using various visible light wavelengths between 435–655 nm to activate the trithiocarbonate compounds. A variety of wavelengths has been used in combination with ZnTPP as ZnTPP has several absorption maxima at 422 nm, 520 nm, 570 nm, and 600 nm (Fig. 3a). Shanmugam *et al.*¹²⁰ used 2-(*n*-butyltrithiocarbonate)-propionic acid (BTPA) as trithiocarbonate to analyze the polymerization rates upon tuning the light wavelength. This study showed that the polymerization with yellow light was the fastest and the polymerization speed decreased from yellow > green > orange > red > blue light whereby the emission of the yellow lamp was centered on the maximum absorption at 570 nm. The group of Pester¹⁰⁹ used



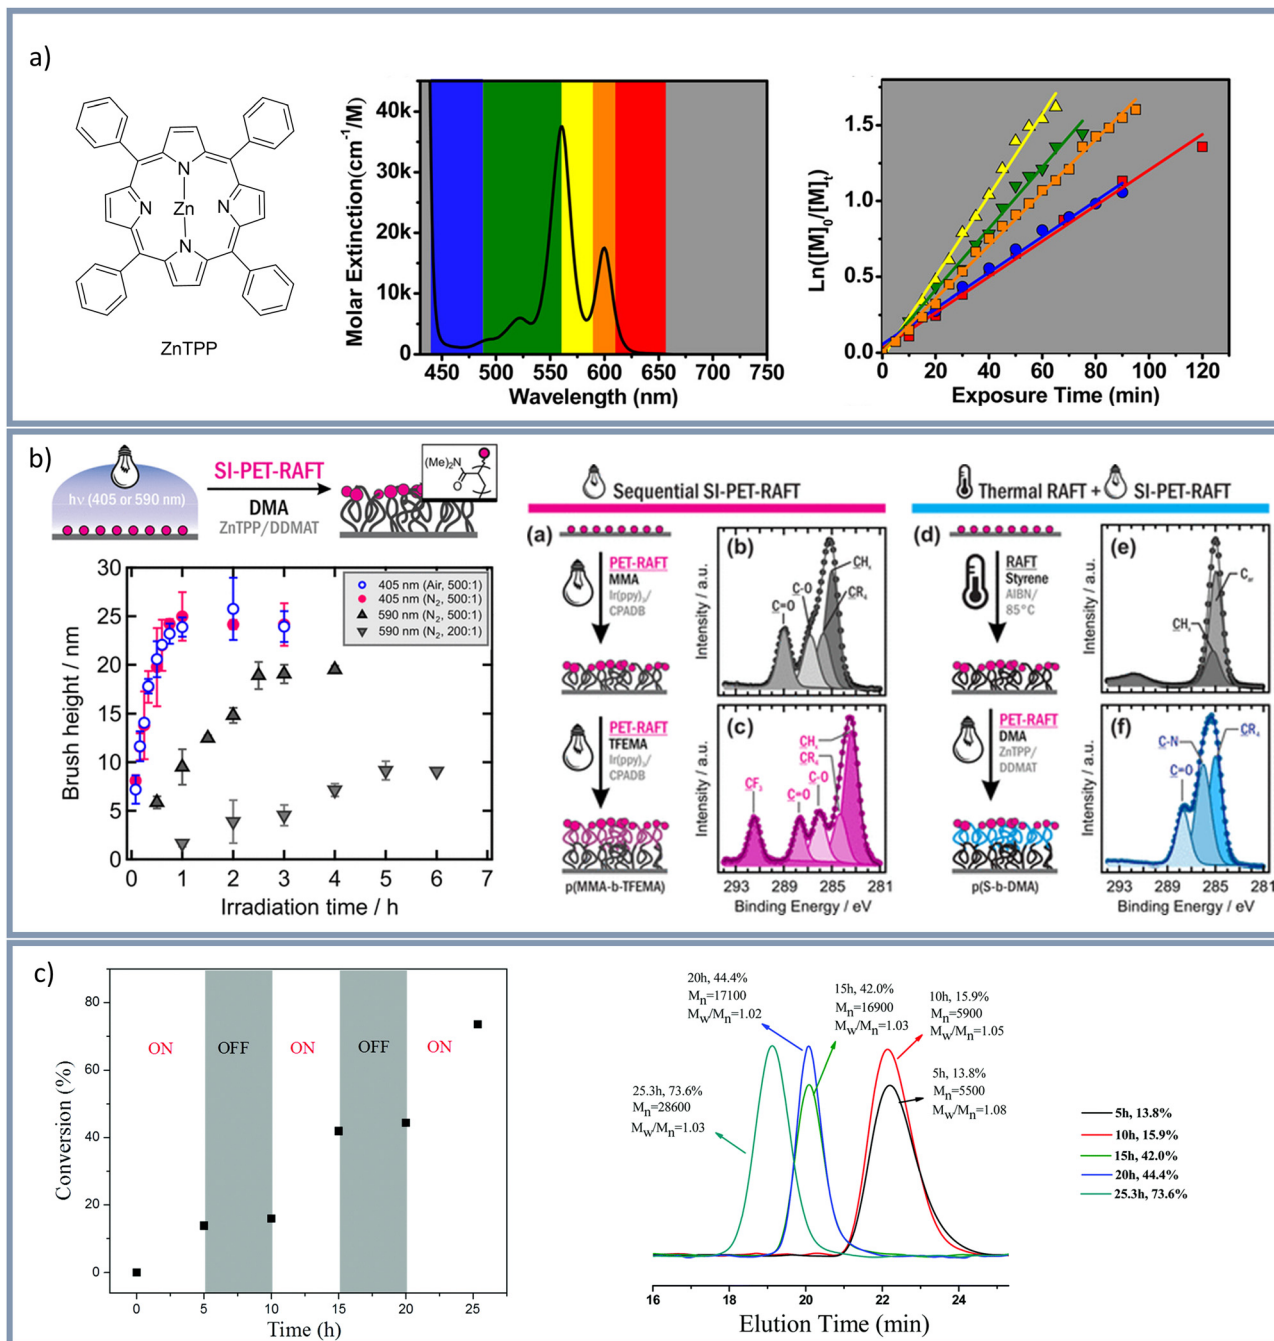


Fig. 3 (a) Molecular structure of the photo catalyst ZnTPP (left). Molar extinction spectrum of ZnTPP with the corresponding LED colors (middle) and plot of $\ln([M]_0/[M]_t)$ vs. exposure time depending on different light wavelengths (right) by Shanmugam *et al.*¹²⁰ Reprinted with the permission from *J. Am. Chem. Soc.*, 2015, **137**, 9174–9185.¹²⁰ Copyright 2015 American Chemical Society. (b) Surface-initiated PET-RAFT by group of Pester¹⁰⁹ Polymer brush thickness vs. irradiation time under inert gas and under air and diblock copolymer synthesis by SI-PET-RAFT. Reprinted with the permission from *ACS Macro Lett.*, 2019, **8**, 374–380.¹⁰⁹ Copyright 2019 American Chemical Society. (c) Visible light mediated RAFT by the group of Pan¹²¹ using PTH as photo catalyst, demonstrating “ON/OFF” control over polymerization. Reproduced with the permission from *Mater. Chem. Front.*, 2017, **1**, 1200–1206¹²¹ with permission from the Chinese Chemical Society (CCS), Institute of Chemistry of Chinese Academy of Sciences (IC), and the Royal Society of Chemistry.

ZnTPP for an oxygen tolerant, surface initiated PET-RAFT (SI-PET-RAFT) under visible light (405 or 590 nm, see Fig. 3b). In this study two different RAFT agents: 2-(dodecylthiocarbonothioylthio)-2-methylpropanoic acid (DDMAT) and 4-cyano-4-(phenylcarbonothioylthio)pentanoic acid (CPADB) were investigated. A higher monomer tolerance for CPADB-functionalized surfaces in com-

bination with the photo catalyst Ir(ppy)₃, showing a strong redox-potential, was described. Furthermore, the synthesis of block copolymers was demonstrated. The group of Pan¹²¹ also used the RAFT agent CPADB for a visible light induced PET-RAFT and demonstrated a temporal control over the polymerization and polymer formation by switching the light on and off (Fig. 3c).



Additionally, the effects of catalyst concentration and light intensity on the polymerization rate were analyzed showing a gradual increase of monomer conversion with catalyst concentration and faster polymerization rate with increasing light intensity. Applying blue light irradiation (460 nm, irradiation time 24 h) Yeow *et al.*¹²² used a ruthenium-based photoredox catalyst ($\text{Ru}(\text{bpy})_3\text{Cl}_2$) to activate a photoinduced PET-RAFT.

But not only metal-based catalysts are suitable for PET-RAFT induced by visible light. Recently, organic catalysts such as Eosin Y^{123,124} and fluorescein¹²⁵ were applied to initiate RET-RAFT polymerizations. Using organic catalysts for a SI-PET-RAFT Kuzmyn *et al.*¹²⁴ prepared antifouling polymer brushes on gold surfaces using three different monomers, namely oligo(ethylene glycol) methyl ether methacrylate (MeOEGMA), carboxybetaine methacrylamide (CBMA), and *N*-(2-hydroxypropyl) methacrylamide (HPMA). In 2016 Shanmugam *et al.*¹¹³ used Bacteriochlorophyll a as organic photoredox catalyst and demonstrated the first PET-RAFT under near-infrared/far-red irradiation (850 nm and 780 nm). Very recently Bellotti and Simounutti¹²⁶ summarized theoretical basics, as well as industrial applications for PET-RAFT.

Unlike the classical RAFT or the PET-RAFT, the iniferter initiated polymerization does not require any additional catalyst which makes it an interesting candidate for polymerization in confined space. This might be an advantage for nanopore functionalization as nanopore accessibility to reagent might be an essential factor for polymerization control. Based on the visible light irradiation of trithiocarbonates (*e.g.* RAFT agents) the polymerization is initiated. Trithiocarbonate compounds possess thiocarbonyl ($\text{C}=\text{S}$) groups. The absorption characteristics of thiocarbonyl-groups are slightly shifted to longer wavelengths, as compared to the absorption of carbonyl ($\text{C}=\text{O}$) groups. Thiocarbonyl groups show an absorption band in UV range at approximately 320 nm (spin allowed) and a second absorption band in the visible light range between 400–550 nm (spin-forbidden). Because of the absorption band at approximately 400–550 nm, compounds with thiocarbonyl groups, for example trithiocarbonate, react to visible light irradiation.²⁹

For the first time, in 2015 the group of Qiao²⁹ used the iniferter benzylododecyl carbonotrithioate (TTC-1) for a light-triggered radical polymerization *via* visible light irradiation at approximately 460 nm in the absence of exogenous photo-initiators or catalysts (Fig. 4a). In this study the synthesis of well-defined poly(acrylamides) and poly(acrylates) was demonstrated. Furthermore, Qiao *et al.* showed that thermal induction of the polymerization could be excluded although the applied LED's heated the reaction mixture. In another example, as well from 2015, the group of Qiao¹²⁷ used trithiocarbonate for a photo-controlled radical polymerization under visible light (460 nm) to generate cross-linked star polymers. Furthermore, Rubens *et al.*²⁵ used a blue light source to initiate a polymerization, which was also controlled by trithiocarbonate. This study demonstrated full monomer conversion within one hour or even shorter reaction time. Therefore, no notable degradation of the trithiocarbonate was observed. The group of Boyer³⁰ reported a photo-controlled radical polymerization using polymerization-induced self-assembly with 4-cyano-4-((dodecylsulfanylthiocarbo-

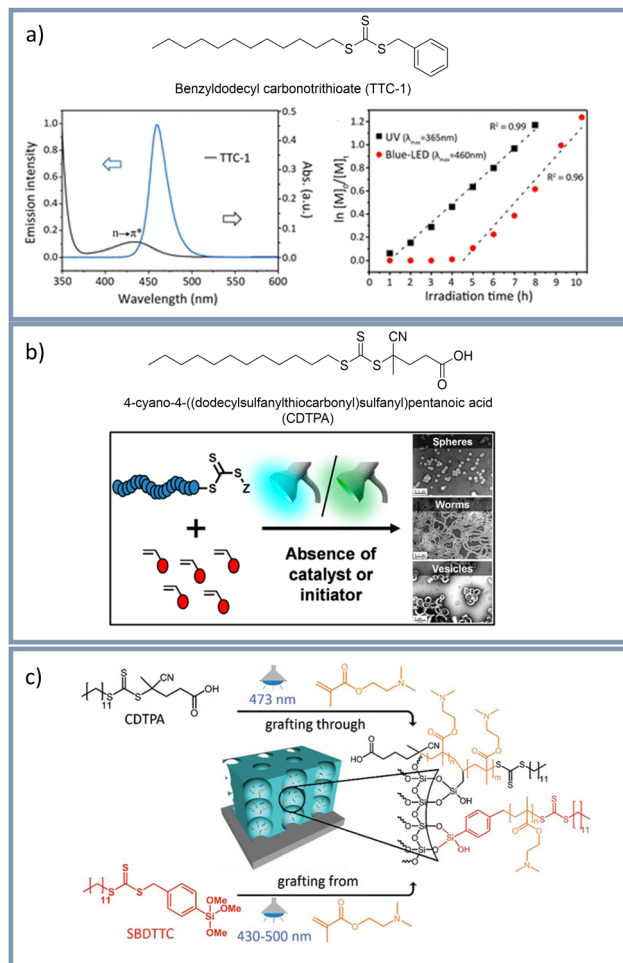


Fig. 4 (a) Visible light induced photo-controlled radical polymerization using the Iniferter TTC-1 for the first time in absence of exogenous photoinitiators or catalysts by the group of Qiao.²⁹ Reprinted with the permission from *Macromolecules*, 2015, **48**, 3864–3872.²⁹ Copyright 2015 American Chemical Society (b) Synthesis of complex polymeric architectures using CDTPA as Iniferter under blue (460 nm) and green (530 nm) light irradiation by the group of Boyer.³⁰ Reprinted with the permission from *ACS Macro Lett.*, 2016, **5**, 558–564.³⁰ Copyright 2016 American Chemical Society. (c) Mesopore functionalization using CDTPA and SBDTTC as iniferter under visible light irradiation by our group.¹³⁰ Reprinted with the permission from *Adv. Funct. Mater.*, 2021, **31**, 2009732.¹³⁰ Copyright 2021 John Wiley & Sons, Inc.

nyl)sulfanyl)pentanoic acid (CDTPA) as iniferter under blue (460 nm) and green (530 nm) light irradiation (Fig. 4b). Probably due to differing degrees of polymerization control using two different light wavelengths, block-copolymer nanoparticles with different morphologies were obtained. In another example CDTPA was also used to synthesize polymeric nanomaterials with various morphologies using visible light irradiation and the organic photoredox catalyst PTH.¹²¹

Despite the recent dynamic developments in visible light induced RAFT including PET-RAFT and iniferter initiated polymerizations in solution and on planar surfaces examples on nanopore functionalization using visible light induced RAFT remain scarce up to date: The group of Wei¹²⁸ used 4-cyano-4-



Highlight

(ethylsulfanylthiocarbonylsulfanyl)pentanoic acid (CEP) for RAFT polymerizations under 480 nm light to functionalized mesoporous silica nanoparticles with zwitterionic polymers. Recently, the first PET-RAFT in mesopores was reported by Joshi and Nebhani.¹²⁹ After synthesizing mesoporous silica particles with an in-built RAFT agent, a visible light induced PET-RAFT was performed using a 50 W LED and Eosin Y as photo catalyst. This PET-RAFT in mesopores was achieved by stepwise co-condensation, using different hydrophobic and hydrophilic monomers. Our research group recently reported an asymmetric mesopore functionalization using a visible light induced PET-RAFT with ZnTPP as photo catalyst.¹³⁰ In another example of our research group a layer-selective functionalization of mesoporous double layered films using the iniferter 4-(*N,N*-diethyldithiocarbamoylmethyl)benzoic acid (BDC) under UV-light irradiation was demonstrated.¹³¹ A visible light induced mesopore functionalization was also performed using two different iniferter approaches: Using the iniferter *S*-*p*-trimeth-oxysilylbenzyl-*S'*-dodecyltrithiocarbonate (SBDTTC) for a grafting from approach and CDTPA for a grafting through approach (Fig. 4c).¹³² Using these two visible light sensitive iniferters in combination with localized surface plasmon resonance from alloy Ag/Au nanoparticles as optical near field method 3D local polymer functionalization was demonstrated.¹³²

Ionic and other controlled polymerizations initiated by visible light

Many examples on visible light induced cationic polymerizations have been reported. One reason for this is probably related to the tolerance of ambient oxygen and water. Most of the reported visible light induced cationic polymerizations are based on onium salt initiators.^{133,134} Examples of typical onium salts for photoinitiated cationic polymerizations are shown in

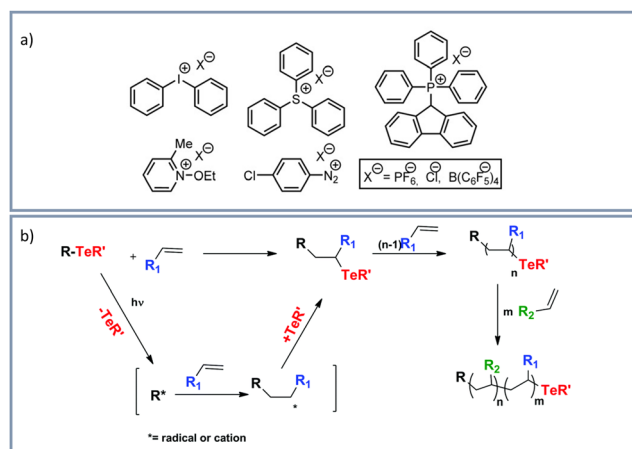


Fig. 5 (a) Typical onium salts for photoinitiated cationic polymerizations by Michaudel *et al.*¹³³ Reprinted with the permission from *Angew. Chem.*, 2017, **129**, 9798–9808.¹³³ Copyright 2017 Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim. (b) Photoinduced organotellurium-mediated polymerization by Kaya *et al.*¹³⁸ Reprinted with the permission from *Polym. Chem.*, 2018, **9**, 5639–5643.¹³⁸ Copyright 2018 Royal Society of Chemistry.

Fig. 5a.¹³³ Mechanistically this polymerization is based on the decay of the excited state of the onium salt after photoexcitation. Thereby, both, a homolytic and a heterolytic cleavage of the onium salt is possible, whereby highly reactive aryl cations and aryl iodine cation radicals are generated. For more information on the mechanism of photoinduced cationic polymerization and the mechanism we refer to the highlight-article “The Discovery and Development of Onium Salt Cationic Photoinitiators” from Crivello in 1999.¹³⁴

Regarding reported examples on cationic salt-based polymerizations, Yilmaz *et al.*¹³⁵ performed a free radical promoted cationic polymerization under irradiation of visible light from 430–490 nm by using thioxanthone-fluorene carboxylic acid or thioxanthone-carbazole as photocatalysts and diphenyliodonium hexafluorophosphate or silver hexa-fluorophosphate as cationic salts. Sari *et al.*¹³⁶ described a surface initiated free radical promoted cationic polymerization on tetrakis(2,4,6-trimethylbenzoyl)silane (TTBS) at room temperature and visible light (> 400 nm) in presence of the onium salts diphenyliodonium hexafluorophosphate and triphenylsulfonium hexafluorophosphate. Also in the presence of onium salts Yilmaz *et al.*¹³⁷ reported a visible light (> 400 nm) induced cationic polymerization by fullerene sensitization. Kaya *et al.*¹³⁸ used organotellurium compounds in the presence of diphenyliodonium hexafluorophosphate for polymerizations initiated by visible light and sunlight (organotellurium-mediated polymerization, Fig. 5b). Crivello¹³⁹ reported a visible light induced cationic polymerization of epoxides with a titanium-complex free radical photoinitiator and diaryliodonium salts. Sangermano and coworkers¹⁴⁰ performed cationic polymerizations using different onium salt photoinitiators. Kerem *et al.*¹⁴¹ used sulfonium salt photoinitiators. For a cationic ring-opening photo-polymerization of epoxide monomers and epoxide functional oligomers an efficient three-component visible light sensitive photoinitiator system was developed. The use of camphorquinone in combination with a benzyl alcohol generates radicals by visible light absorbance.¹⁴² Combining free radical and cationic polymerizations of vinyl monomers and cyclic ethers, initiated by visible light (400–500 nm), conjugated microporous polymeric networks containing thioxanthone groups were obtained.¹⁴³

Besides these examples of cationic polymerizations, combined with free radical photoinitiators, it is also possible to combine free radical promoted cationic polymerization with controlled radical polymerizations: For example, the group of Yagci¹⁴⁴ used Mn₂(CO)₁₀ as radical source and synthesized block copolymers by the combination from ATRP with visible light induced free radical promoted cationic polymerization. In a further example, the group of Yagci¹⁴⁵ synthesized amphiphilic hyperbranched macromolecular structures in presence of Mn₂(CO)₁₀ by using the visible light induced self-condensing vinyl copolymerization of three methacrylates. Mn₂(CO)₁₀ for visible light induced polymerizations was not only applied in solution, furthermore surface functionalization was achieved: Xiong *et al.*¹⁴⁶ described a visible light induced surface grafting polymerization with the use of Mn₂(CO)₁₀ on gold surfaces. The polymer-film thickness was controlled by variation of the



irradiation time. The group of Chen¹⁴⁷ reported the surface functionalization of poly(dimethylsiloxane) by visible light induced polymerization with $\text{Mn}_2(\text{CO})_{10}$. Combining a visible light-induced free radical polymerization with a ROMP and hydrobromination the group of Yagci^{148,149} prepared a copolymer by grafting from using $\text{Mn}_2(\text{CO})_{10}$ and visible light irradiation. $\text{Mn}_2(\text{CO})_{10}$ as photo catalyst was also used for a visible light induced iodine transfer polymerizations (ITP) at 463 nm by Koumura *et al.*¹⁵⁰ ITP is a controlled radical polymerization, which involves vinyl monomer, a conventional initiator and an iodinated chain transfer agent.¹⁵¹ The general mechanism of the polymerization using $\text{Mn}_2(\text{CO})_{10}$ is shown in Fig. 6a.¹⁵¹ The applications of visible light induced photo initiation based on $\text{Mn}_2(\text{CO})_{10}$ was summarized by the group of Yagci in 2016.¹⁵¹ Furthermore, visible-light induced ITP have been realized using an Ir(III) complex (Fig. 6b).¹⁵² Fors and Hawker¹⁵³ portrayed a visible light induced living radical polymerization with ppm amounts of the photocatalyst *fac*-[Ir(ppy)₃]. The suggested mechanism of the polymerization is shown in Fig. 6c.

These examples represent a selection among the manifold studies on visible light induced polymerizations based on cationic polymerization, whereby especially polymerizations based on onium salts or $\text{Mn}_2(\text{CO})_{10}$ are frequently used. Most of the studies on this type of polymerization were performed at wavelengths below 600 nm and in solution. Going towards red light irradiation, the group of Fouassier reported the development of cationic polymerizations and showed the possibility to use various wavelengths, including red light irradiation.¹⁵⁴ Despite the plenty examples on visible light induced cationic polymerizations in

solution and even on surfaces, studies on polymer functionalization of nanoporous materials using visible light induced cationic polymerizations remain unreached (Fig. 8).

Visible light induced ROMP

Besides visible-light induced cationic polymerizations and ITP visible-light induced ROMP represents another, complementary polymerization technique beyond radical polymerization. Only a few examples on visible light induced ROMP have been demonstrated. In general, visible light induced ROMP are still relatively scarce, and so far limited to solution polymerizations. In the traditional ROMP metal-complexes, *e.g.* Ru-, W-, or Mo-alkylidene complexes, are used as catalysts.¹⁵⁵ Also organocatalyzed ROMPs have been reported, which use vinyl ethers as initiators^{156,157} In 2015 the group of Boydston¹⁵⁶ reported the first metal free ROMP using blue-light emitting LEDs (450–480 nm). The used photoredox mediators compatible with this blue-light LED irradiation are shown in Fig. 7a. Theunissen *et al.*¹⁵⁸ published a ROMP and photolithographic olefin metathesis polymerization (PLOMP) using blue light. Using divinyl ether initiators and a photoredox catalyst to polymerize norbornene upon 450–480 nm light irradiation, the group of Boydston¹⁵⁷ successfully performed a visible light induced ROMP. Fig. 7b shows the used divinyl ethers (1 and 2) and the pyrylium photocatalyst (4). Recently Eivig *et al.* reported ROMP under 420 nm irradiation as suitable for 3D applications.¹⁵⁹

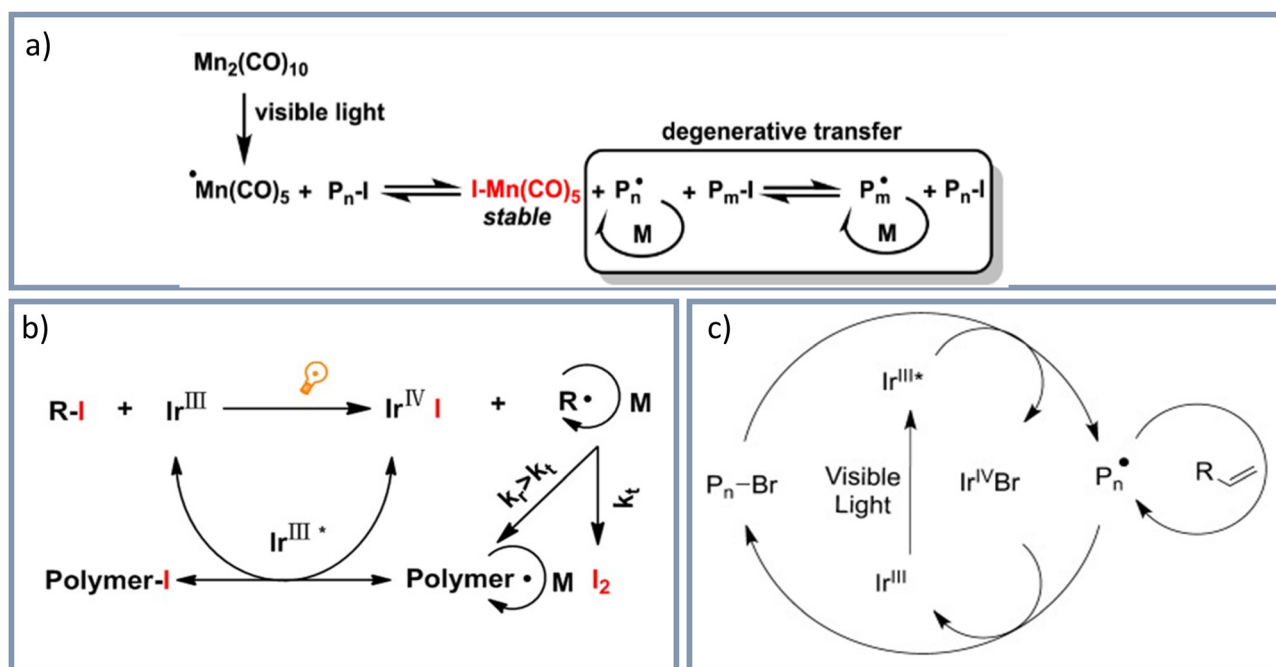


Fig. 6 (a) Mechanism of photo induced ITP with $\text{Mn}_2(\text{CO})_{10}$ /alkyl iodide.¹⁵¹ Reprinted with permission from *Polym. Int.*, 2016, **65**, 1001–1014. Copyright 2016 John Wiley & Sons, Inc. (b) Visible-light induced ITP with Ir(III) complex.¹⁵² Reprinted with permission from *J. Polym. Sci., Part A: Polym. Chem.*, 2014, **52**, 3283–3291. Copyright 2014 John Wiley & Sons, Inc. (c) Suggested mechanisms of the visible light induced polymerization using an Ir-based photoredox catalyst.¹⁵³ Reprinted with permission from *Angew. Chem., Int. Ed.*, 2012, **51**, 8850–8853. Copyright 2021 John Wiley & Sons, Inc.



Highlight

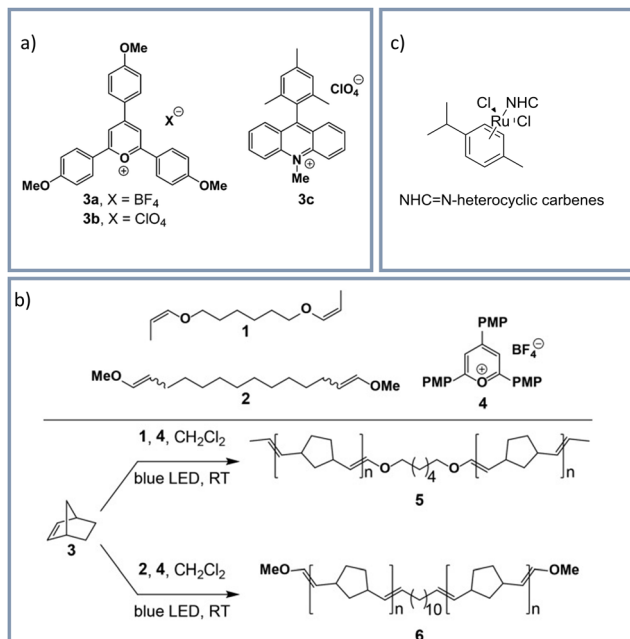


Fig. 7 (a) Photoredox mediators for metal free ROMP under blue light irradiation by the group of Boydston.¹⁵⁶ Reprinted with the permission from *J. Am. Chem. Soc.*, 2015, **137**, 1400–1403. Copyright 2015 American Chemical Society. (b) Photo catalyzed ROMP by the group of Boydston¹⁵⁷ Reprinted with the permission from *J. Polym. Sci., Part A: Polym. Chem.*, 2017, **55**, 2977–2982.¹⁵⁷ Copyright 2017 John Wiley & Sons, Inc. (c) General structure of visible light catalysts for ROMP.¹⁶⁰ Reprinted with permission from *Synlett*, 2016, **27**, 203–214.¹⁶⁰ Copyright 2016, Rights Managed by Georg Thieme Verlag KG.

Catalysts with the general structure shown in Fig. 7c, absorb at 450 nm and can also be used for visible light control of ROMP.¹⁶⁰

Examples on nanoporous material functionalization using classical ROMP remain scarce and examples on visible light induced ROMP in nanopores have not yet been reported. For classical ROMP Mohite *et al.*¹⁶¹ polymerized free norbornene using ROMP in nanoporous silica nanoparticles, whereby it was bound to surface-grafted norbornene by using a crosslinking mechanism. Our research group reported on ROMP being used to functionalize nanopores with 5-norbornene-2-carboxylic acid pentafluorophenyl ester¹⁶² as well as with spiropyran and spirooxazine substituted polynorbornene homopolymers.¹⁶³ Plenio and colleagues¹⁶⁴ showed an alternative approach when covalently binding the catalyst to a silica nanoparticle surface followed by a SI-ROMP in presence of monomer in solution.

Conclusions

In summary, research on visible light induced polymerizations has been dynamically evolving over the last years. In particular, many examples of visible-light induced cationic polymerizations, ATRP, and RAFT in solution and on planar surfaces have been reported mainly within the last two decades (Fig. 8a). Main research activities within the last years have been focused on broadening the wavelengths range to cover the entire range of visible light, *e.g.* using metal photo catalysts. Subsequently, the

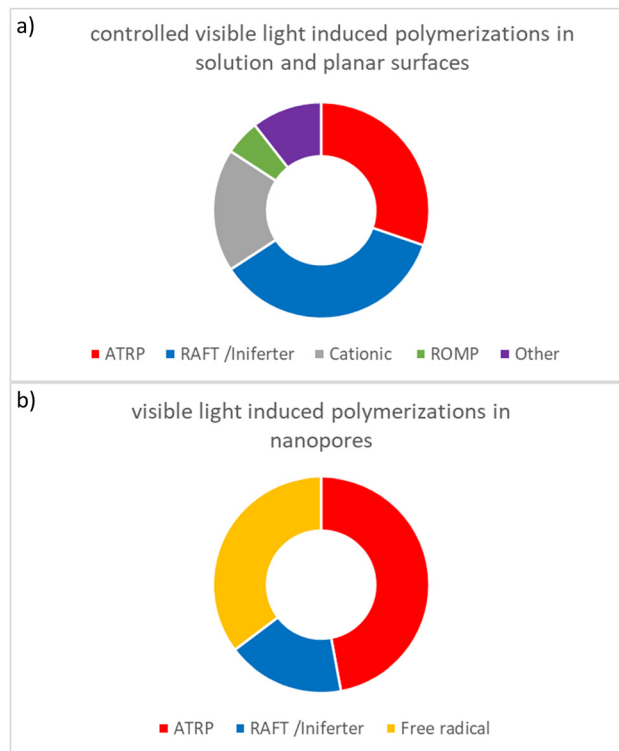


Fig. 8 Comparative summary of (a) controlled visible light induced polymerizations in solution and on planar surfaces, mentioned in this article (in total 76 references) and (b) first examples on visible light induced polymerizations in nanopores as cited in this article (in total 17 references).

number of reported studies on visible light induced polymerization increased and the wavelength range was shifted significantly into the visible wavelength range. Furthermore, the reduction of these metal photo catalysts in the reaction was strongly investigated resulting in synthesis strategies allowing metal-free visible light controlled polymerizations with increasing number of reported studies in recent years. Although the number of examples is still limited, visible light induced controlled radical polymerizations such as visible-light induced ATRP, visible-light induced PET-RAFT, dye-sensitized polymerizations, and visible light induced iniferter initiated polymerizations were successfully transferred to nanopore functionalization (Fig. 8b). ATRP is the most frequently used visible light induced polymerization in nanopores, with a contribution of 47% of the cited references in this review. Nevertheless, visible light induced PET-RAFT is especially significant when considering that only very recently in 2022 the first examples of PET-RAFT in nanopores was reported. The differences between the polymerization techniques in solution and on planar surfaces as compared to nanopores as well clearly demonstrates the challenges in nanopore visible-light polymerization with respect to ionic and ROMP polymerization. Visible light induced controlled radical polymerizations are envisioned to be of special interest with respect to automated and advanced material fabrication and functionalization strategies. Here in particular the potential enabling high local control on polymer placement in nanoporous materials is of interest. Mechanistically, the question of how confinement, local concentration variations as well as



nanopore accessibility and transport influence such visible light induced polymerization still bares many open questions. In this context recent work on confinement controlled catalysis^{165–167} together with theoretical work on ion concentration profiles along nanopore cross sections¹⁴ points towards deeper understanding of confinement influences on reactions and represents a first starting point towards a rational confinement-controlled design. However, compared to the many examples in solution and even on planar surfaces, the development of visible light induced polymerizations for nanopore functionalization is still in its infancy (Fig. 8) but inherits great potential especially for automated polymer writing, highly precise polymer placement, or additive manufacturing.

Author contributions

Claire Förster: writing original draft, visualization, investigation. Annette-Andrieu-Brunsen: acquisition of funding, supervision and assistance with manuscript writing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors acknowledge funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation program (grant agreement No 803758).

References

- W. Lu, Y. Cao and G. Qing, Recent Advances in the Modification and Characterization of Solid-State Nanopores, *Chem. – Asian J.*, 2022, e202200675.
- R. Brilmayer, C. Förster, L. Zhao and A. Andrieu-Brunsen, Recent trends in nanopore polymer functionalization, *Curr. Opin. Biotechnol.*, 2020, **63**, 200–209.
- R. Pardehkorram and A. Andrieu-Brunsen, Pushing the limits of nanopore transport performance by polymer functionalization, *Chem. Commun.*, 2022, **58**, 5188–5204.
- L. Fu and J. Zhai, Biomimetic stimuli-responsive nanochannels and their applications, *Electrophoresis*, 2019, **40**, 2058–2074.
- Z. Zhu, D. Wang, Y. Tian and L. Jiang, Ion/Molecule Transportation in Nanopores and Nanochannels: From Critical Principles to Diverse Functions, *J. Am. Chem. Soc.*, 2019, **141**, 8658–8669.
- Y. A. Perez Sirkin, M. Tagliacruzchi and I. Szeleifer, Transport in nanopores and nanochannels: some fundamental challenges and nature-inspired solutions, *Mater. Today Adv.*, 2020, **5**, 100047.
- S. Alberti, G. J. A. A. Soler-Illia and O. Azzaroni, Gated supramolecular chemistry in hybrid mesoporous silica nanoarchitectures: controlled delivery and molecular transport in response to chemical, physical and biological stimuli, *Chem. Commun.*, 2015, **51**, 6050–6075.
- Z. Zhang, L. Wen and L. Jiang, Bioinspired smart asymmetric nanochannel membranes, *Chem. Soc. Rev.*, 2018, **47**, 322–356.
- H. Zhang, Y. Tian and L. Jiang, From symmetric to asymmetric design of bio-inspired smart single nanochannels, *Chem. Commun.*, 2013, **49**, 10048–10063.
- X. Hou, W. Guo and L. Jiang, Biomimetic smart nanopores and nanochannels, *Chem. Soc. Rev.*, 2011, **40**, 2385–2401.
- L. Wen, X. Hou, Y. Tian, F.-Q. Nie, Y. Song, J. Zhai and L. Jiang, Bioinspired smart gating of nanochannels toward photoelectric-conversion systems, *Adv. Mater.*, 2010, **22**, 1021–1024.
- Ç. K. Söz, S. Trosien and M. Biesalski, Janus Interface Materials: A Critical Review and Comparative Study, *ACS Mater. Lett.*, 2020, **2**, 336–357.
- S. Qin, K. Huang and I. Szeleifer, Design of Multifunctional Nanopore Using Polyampholyte Brush with Composition Gradient, *ACS Nano*, 2021, **15**(11), 17678–17688.
- K. Huang and I. Szeleifer, Design of multifunctional nanogate in response to multiple external stimuli using amphiphilic diblock copolymer, *J. Am. Chem. Soc.*, 2017, **139**, 6422–6430.
- M. Szwarc, 'Living' Polymers, *Nature*, 1956, **178**, 1168–1169.
- K. Matyjaszewski, Atom Transfer Radical Polymerization: From Mechanisms to Applications, *Isr. J. Chem.*, 2012, **52**, 206–220.
- M. Marin-Suarez, A. L. Medina-Castillo, J. F. Fernandez-Sanchez and A. Fernandez-Gutierrez, Atom-Transfer Radical Polymerisation (ATRP) as a Tool for the Development of Optical Sensing Phases, *Isr. J. Chem.*, 2012, **52**, 264–275.
- J. Chiefari, Y. K. B. Chong, F. Ercole, J. Krstina, J. Jeffery, T. P. T. Le, R. T. A. Mayadunne, G. F. Meijs, C. L. Moad, G. Moad, E. Rizzardo and S. H. Thang, Living Free-Radical Polymerization by Reversible Addition-Fragmentation Chain Transfer: The RAFT Process, *Macromolecules*, 1998, 5559–5562.
- C. J. Hawker, Molecular Weight Control by a "Living" Free-Radical Polymerization Process, *J. Am. Chem. Soc.*, 1994, **116**, 11185–11186.
- U. Meyer, F. Svec, J. M. J. Fréchet, C. J. Hawker and K. Irgum, Use of Stable Free Radicals for the Sequential Preparation and Surface Grafting of Functionalized Macroporous Monoliths, *Macromolecules*, 2000, **33**, 7769–7775.
- T. Otsu, M. Yoshida and T. Tazaki, A model for living radical polymerization, *Die Makromol. Chem., Rapid Commun.*, 1982, **3**, 133–140.
- J. C. Tom, R. Brilmayer, J. Schmidt and A. Andrieu-Brunsen, Optimisation of Surface-Initiated Photoiniferter-Mediated Polymerisation under Confinement, and the Formation of Block Copolymers in Mesoporous Films, *Polymers*, 2017, **9**, 539.
- L. Silies, H. Didzoleit, C. Hess, B. Stühn and A. Andrieu-Brunsen, Mesoporous Thin Films, Zwitterionic Monomers, and Iniferter-Initiated Polymerization: Polymerization in a Confined Space, *Chem. Mater.*, 2015, **27**, 1971–1981.
- K. Parkatidis, H. S. Wang, N. P. Truong and A. Anastasaki, Recent Developments and Future Challenges in Controlled Radical Polymerization: A 2020 Update, *Chem*, 2020, **6**, 1575–1588.
- M. Rubens, P. Latsrisaeng and T. Junkers, Visible light-induced iniferter polymerization of methacrylates enhanced by continuous flow, *Polym. Chem.*, 2017, **8**, 6496–6505.
- G. E. M. Criszena and P. Melchiorre, Chemistry glows green with photoredox catalysis, *Nat. Commun.*, 2020, **11**, 803.
- T. P. Yoon, M. A. Ischay and J. Du, Visible light photocatalysis as a greener approach to photochemical synthesis, *Nat. Chem.*, 2010, **2**, 527–532.
- C. A. Boyer and G. M. Miyake, Polymers and Light, *Macromol. Rapid Commun.*, 2017, **38**, 1700327.
- T. G. McKenzie, Q. Fu, E. H. H. Wong, D. E. Dunstan and G. G. Qiao, Visible Light Mediated Controlled Radical Polymerization in the Absence of Exogenous Radical Sources or Catalysts, *Macromolecules*, 2015, **48**, 3864–3872.
- J. Yeow, O. R. Sugita and C. Boyer, Visible Light-Mediated Polymerization-Induced Self-Assembly in the Absence of External Catalyst or Initiator, *ACS Macro Lett.*, 2016, **5**, 558–564.
- N. Corrigan, S. Shanmugam, J. Xu and C. Boyer, Photocatalysis in organic and polymer synthesis, *Chem. Soc. Rev.*, 2016, **45**, 6165–6212.
- P. R. Judzewitsch, N. Corrigan, F. Trujillo, J. Xu, G. Moad, C. J. Hawker, E. H. H. Wong and C. Boyer, High-Throughput Process for the Discovery of Antimicrobial Polymers and Their Upscaled Production via Flow Polymerization, *Macromolecules*, 2020, **53**, 631–639.
- S. Oliver, L. Zhao, A. J. Gormley, R. Chapman and C. Boyer, Living in the Fast Lane—High Throughput Controlled/Living Radical Polymerization, *Macromolecules*, 2019, **52**, 3–23.
- Z. Li, Z. Han, M. H. Stenzel and R. Chapman, A High Throughput Approach for Designing Polymers That Mimic the TRAIL Protein, *Nano Lett.*, 2022, **22**, 2660–2666.



- 35 R. Li, S. Zhang, Q. Li, G. G. Qiao and Z. An, An Atom-Economic Enzymatic Cascade Catalysis for High-Throughput RAFT Synthesis of Ultrahigh Molecular Weight Polymers, *Angew. Chem.*, 2022, **134**, e202213396.
- 36 G. Ng, J. Yeow, R. Chapman, N. Isahak, E. Wolvetang, J. J. Cooper-White and C. Boyer, Pushing the Limits of High Throughput PET-RAFT Polymerization, *Macromolecules*, 2018, **51**, 7600–7607.
- 37 R. Upadhyaya, A. Punia, M. J. Kanagala, L. Liu, M. Lamm, T. A. Rhodes and A. J. Gormley, Automated PET-RAFT Polymerization Towards Pharmaceutical Amorphous Solid Dispersion Development, *ACS Appl. Polym. Mater.*, 2021, **3**, 1525–1536.
- 38 Q. Liu, L. Fang, G. Yu, D. Wang, C.-L. Xiao and K. Wang, Detection of DNA base modifications by deep recurrent neural network on Oxford Nanopore sequencing data, *Nat. Commun.*, 2019, **10**, 2449.
- 39 K. Matyjaszewski and T. P. Davis, *Handbook of Radical Polymerization*, John Wiley & Sons, Inc, Hoboken, NJ, USA, 2002.
- 40 H. J. Hageman, Photoinitiators for free radical polymerization, *Prog. Org. Coat.*, 1985, **13**, 123–150.
- 41 S. M. Müller, S. Schlögl, T. Wiesner, M. Haas and T. Griesser, Recent Advances in Type I Photoinitiators for Visible Light Induced Photopolymerization, *ChemPhotoChem*, 2022, **6**, e202200091.
- 42 X. He, Y. Gao, J. Nie and F. Sun, Methyl Benzoylformate Derivative Norrish Type I Photoinitiators for Deep-Layer Photocuring under Near-UV or Visible LED, *Macromolecules*, 2021, **54**, 3854–3864.
- 43 J. Maier, S. M. Müller, A. Torvisco, G. Glotz, R. C. Fischer, T. Griesser, A.-M. Kelterer and M. Haas, Isolable Stannolates Enable the Synthesis of Visible-Light Photoinitiators, *ChemPhotoChem*, 2022, **6**, e202100213.
- 44 J. Lalevée and J. P. Fouassier, *Dyes and Chromophores in Polymer Science*, Wiley, Hoboken, 2015.
- 45 C. Deeb, C. Ecoffet, R. Bachelot, J. Plain, A. Bouhelier and O. Soppera, Plasmon-Based Free-Radical Photopolymerization: Effect of Diffusion on Nanolithography Processes, *J. Am. Chem. Soc.*, 2011, **133**, 10535–10542.
- 46 J. P. Fouassier and L. Jacques, *Photoinitiators for Polymer Synthesis: Scope, Reactivity and Efficiency*, Wiley-VCH Verlag GmbH & Co. KGaA, 2012.
- 47 J. Kabatc and J. Pączkowski, Monomeric asymmetric two- and three-cationic monomethine cyanine dyes as novel photoinitiators for free-radical polymerization, *Dyes Pigm.*, 2010, **86**, 133–142.
- 48 N. Herzog, J. Kind, C. Hess and A. Andrieu-Brunsen, Surface plasmon & visible light for polymer functionalization of mesopores and manipulation of ionic permselectivity, *Chem. Commun.*, 2015, **51**, 11697–11700.
- 49 K. Sun, C. Pigot, Y. Zhang, T. Borjigin, F. Morlet-Savary, B. Graff, M. Nechab, P. Xiao, F. Dumur and J. Lalevée, Sunlight Induced Polymerization Photoinitiated by Novel Push–Pull Dyes: Indane-1,3-Dione, 1H-Cyclopenta[b]Naphthalene-1,3(2H)-Dione and 4-Dimethoxyphenyl-1-Allylidene Derivatives, *Macromol. Chem. Phys.*, 2022, **223**, 2100439.
- 50 F. Kameche, W. Heni, S. Telitel, L. Vidal, S. Marguet, L. Douillard, C. Fiorini-Debuisschert, R. Bachelot and O. Soppera, Probing Plasmon-Induced Chemical Mechanisms by Free-Radical Nanophotopolymerization, *J. Phys. Chem. C*, 2021, **125**, 8719–8731.
- 51 D. John, R. Mohammadi, N. Vogel and A. Andrieu-Brunsen, Surface-Plasmon- and Green-Light-Induced Polymerization in Mesoporous Thin Silica Films, *Langmuir*, 2020, **36**, 1671–1679.
- 52 M. Stanzel, L. Zhao, R. Mohammadi, R. Pardehkhorrām, U. Kunz, N. Vogel and A. Andrieu-Brunsen, Simultaneous Nanolocal Polymer and In Situ Readout Unit Placement in Mesoporous Separation Layers, *Anal. Chem.*, 2021, **93**, 5394–5402.
- 53 B. Harke, P. Bianchini, F. Brandi and A. Diaspro, Photopolymerization inhibition dynamics for sub-diffraction direct laser writing lithography, *ChemPhysChem*, 2012, **13**, 1429–1434.
- 54 J. B. Mueller, J. Fischer, F. Mayer, M. Kadac and M. Wegener, Polymerization kinetics in three-dimensional direct laser writing, *Adv. Mater.*, 2014, **26**, 6566–6571.
- 55 A. Selimis, V. Mironov and M. Farsari, Direct laser writing: Principles and materials for scaffold 3D printing, *Microelectron. Eng.*, 2015, **132**, 83–89.
- 56 Y. Wu, M. C. Simpson and J. Jin, 3D Printing of Thiol-Yne Photoresins through Visible Light Photoredox Catalysis, *ChemistrySelect*, 2022, **7**, e202200319.
- 57 F. Dumur, Recent advances on visible light Thiophene-based photoinitiators of polymerization, *Eur. Polym. J.*, 2022, **169**, 111120.
- 58 Y. Xu, G. Noirbent, D. Brunel, Z. Ding, D. Gimes, B. Graff, P. Xiao, F. Dumur and J. Lalevée, Novel ketone derivative-based photoinitiating systems for free radical polymerization under mild conditions and 3D printing, *Polym. Chem.*, 2020, **11**, 5767–5777.
- 59 X. Zhang, S. Keck, Y. Qi, S. Baudis and Y. Zhao, Study on Modified Dealkaline Lignin as Visible Light Macromolecular Photoinitiator for 3D Printing, *ACS Sustainable Chem. Eng.*, 2020, **8**(29), 10959–10970.
- 60 J. Zhang, K. Launay, N. S. Hill, D. Zhu, N. Cox, J. Langley, J. Lalevée, M. H. Stenzel, M. L. Coote and P. Xiao, Disubstituted Aminoanthraquinone-Based Photoinitiators for Free Radical Polymerization and Fast 3D Printing under Visible Light, *Macromolecules*, 2018, **51**, 10104–10112.
- 61 M. S. Eisen, Controlled Radical Polymerizations, *Isr. J. Chem.*, 2012, **52**, 204–205.
- 62 X. Huang and M. J. Wirth, Surface-Initiated Radical Polymerization on Porous Silica, *Anal. Chem.*, 1997, **69**, 4577–4580.
- 63 M. Kruk, Surface-Initiated Controlled Radical Polymerization in Ordered Mesoporous Silicas, *Isr. J. Chem.*, 2012, **52**, 246–255.
- 64 Q. Fu, G. V. R. Rao, L. K. Ista, Y. Wu, B. P. Andrzejewski, L. A. Sklar, T. L. Ward and G. P. López, Control of Molecular Transport Through Stimuli-Responsive Ordered Mesoporous Materials, *Adv. Mater.*, 2003, **15**, 1262–1266.
- 65 H. Bayat, M. Raoufi, I. Zamrik and H. Schönherr, Poly(diethylene glycol methylether methacrylate) Brush-Functionalized Anodic Alumina Nanopores: Curvature-Dependent Polymerization Kinetics and Nanopore Filling, *Langmuir*, 2020, **36**, 2663–2672.
- 66 L. Cao, T. Man, J. Zhuang and M. Kruk, Poly(N-isopropylacrylamide) and poly(2-(dimethylamino)ethyl methacrylate) grafted on an ordered mesoporous silica surface using atom transfer radical polymerization with activators regenerated by electron transfer, *J. Mater. Chem.*, 2012, **22**, 6939.
- 67 A. Martin, G. Morales, F. Martinez, R. van Grieken, L. Cao and M. Kruk, Acid hybrid catalysts from poly(styrenesulfonic acid) grafted onto ultra-large-pore SBA-15 silica using atom transfer radical polymerization, *J. Mater. Chem.*, 2010, **20**, 8026.
- 68 A. Calvo, B. Yameen, F. J. Williams, O. Azzaroni and G. J. A. Soler-Illia, Facile molecular design of hybrid functional assemblies with controllable transport properties: mesoporous films meet polyelectrolyte brushes, *Chem. Commun.*, 2009, 2553–2555.
- 69 M. Kruk, B. Dufour, E. B. Celcer, T. Kowalewski, M. Jaroniec and K. Matyjaszewski, Grafting Monodisperse Polymer Chains from Concave Surfaces of Ordered Mesoporous Silicas, *Macromolecules*, 2008, **41**, 8584–8591.
- 70 S. Alberti, J. Giussi, O. Azzaroni and G. J. A. Soler-Illia, A Comparative Study of PMETAC-Modified Mesoporous Silica and Titania Thin Films for Molecular Transport Manipulation, *Polymers*, 2022, **14**, 4823.
- 71 M. Barsbay and O. Güven, Grafting in confined spaces: Functionalization of nanochannels of track-etched membranes, *Radiat. Phys. Chem.*, 2014, **105**, 26–30.
- 72 K. Daumann, S. Frost and M. Ulbricht, Tunable and switchable nanoparticle separation with thermo-responsive track-etched membranes prepared by controlled surface-initiated polymerization of poly(N-isopropylacrylamide), *RSC Adv.*, 2020, **10**, 21028–21038.
- 73 A. Friebe and M. Ulbricht, Controlled pore functionalization of poly(ethylene terephthalate) track-etched membranes via surface-initiated atom transfer radical polymerization, *Langmuir*, 2007, **23**, 10316–10322.
- 74 D. A. Corbin and G. M. Miyake, Photoinduced Organocatalyzed Atom Transfer Radical Polymerization (O-ATRP): Precision Polymer Synthesis Using Organic Photoredox Catalysis, *Chem. Rev.*, 2022, **122**, 1830–1874.
- 75 D. Konkolewicz, K. Schröder, J. Buback, S. Bernhard and K. Matyjaszewski, Visible Light and Sunlight Photoinduced ATRP with ppm of Cu Catalyst, *ACS Macro Lett.*, 2012, **1**, 1219–1223.
- 76 M. Ciftci, M. A. Tasdelen and Y. Yagci, Sunlight induced atom transfer radical polymerization by using dimanganese decacarbonyl, *Polym. Chem.*, 2014, **5**, 600–606.
- 77 X. Pan, N. Malhotra, A. Simakova, Z. Wang, D. Konkolewicz and K. Matyjaszewski, Photoinduced Atom Transfer Radical Polymerization with ppm-Level Cu Catalyst by Visible Light in Aqueous Media, *J. Am. Chem. Soc.*, 2015, **137**, 15430–15433.
- 78 N. J. Treat, B. P. Fors, J. W. Kramer, M. Christianson, C.-Y. Chiu, J. Read de Alaniz and C. J. Hawker, Controlled Radical



- Polymerization of Acrylates Regulated by Visible Light, *ACS Macro Lett.*, 2014, 3, 580–584.
- 79 X. Liu, Y. Ni, J. Wu, H. Jiang, Z. Zhang, L. Zhang, Z. Cheng and X. Zhu, A sustainable photocontrolled ATRP strategy: facile separation and recycling of a visible-light-mediated catalyst *fac*-[Ir(ppy)₃], *Polym. Chem.*, 2018, 9, 584–592.
- 80 G. Szczepaniak, J. Jeong, K. Kapil, S. Dadashi-Silab, S. S. Yerneni, P. Ratajczyk, S. Lathwal, D. J. Schild, S. R. Das and K. Matyjaszewski, Open-air green-light-driven ATRP enabled by dual photoredox/copper catalysis, *Chem. Sci.*, 2022, 13, 11540–11550.
- 81 N. J. Treat, H. Sprafke, J. W. Kramer, P. G. Clark, B. E. Barton, J. Read de Alaniz, B. P. Fors and C. J. Hawker, Metal-free atom transfer radical polymerization, *J. Am. Chem. Soc.*, 2014, 136, 16096–16101.
- 82 G. M. Miyake and J. C. Theriot, Perylene as an Organic Photocatalyst for the Radical Polymerization of Functionalized Vinyl Monomers through Oxidative Quenching with Alkyl Bromides and Visible Light, *Macromolecules*, 2014, 47, 8255–8261.
- 83 M. A. Tasdelen, M. Ciftci and Y. Yagci, Visible Light-Induced Atom Transfer Radical Polymerization, *Macromol. Chem. Phys.*, 2012, 213, 1391–1396.
- 84 X.-D. Liu, L. Zhang, Z.-P. Cheng and X. Zhu, Metal-Free Photo-induced Electron Transfer - Atom Transfer Radical Polymerization (PET-ATRP) via a Visible Light Organic Photocatalyst, *Polym. Chem.*, 2016, 7, 689–700.
- 85 Y. Yagci, G. Yilmaz, C. Kütahya and S. Aykac, LED and Visible Light-induced Metal Free ATRP Using Reducible Dyes in the Presence of Amines, *Polym. Chem.*, 2016, 7, 6094–6098.
- 86 L. Wang, R. Li and K. A. I. Zhang, Atom Transfer Radical Polymerization (ATRP) Catalyzed by Visible Light-Absorbed Small Molecule Organic Semiconductors, *Macromol. Rapid Commun.*, 2018, 39, 1800466.
- 87 Y. Xu, G. Li, Y. Hu and Y. Wang, Synthesis of Poly(N-isopropylacrylamide)-Block -Poly(tert -Butyl Methacrylate) Block Copolymer by Visible Light-Induced Metal-Free Atom Transfer Radical Polymerization, *Macromol. Chem. Phys.*, 2018, 219, 1800192.
- 88 L. Qiao, M. Zhou, G. Shi, Z. Cui, X. Zhang, P. Fu, M. Liu, X. Qiao, Y. He and X. Pang, Ultrafast Visible-Light-Induced ATRP in Aqueous Media with Carbon Quantum Dots as the Catalyst and Its Application for 3D Printing, *J. Am. Chem. Soc.*, 2022, 144, 9817–9826.
- 89 S. Dadashi-Silab, K. Kim, F. Lorandi, G. Szczepaniak, S. Kramer, L. Peteanu and K. Matyjaszewski, Red-Light-Induced, Copper-Catalyzed Atom Transfer Radical Polymerization, *ACS Macro Lett.*, 2022, 11, 376–381.
- 90 C. Kütahya, C. Schmitz, V. Strehmel, Y. Yagci and B. Strehmel, Near-Infrared Sensitized Photoinduced Atom-Transfer Radical Polymerization (ATRP) with a Copper(II) Catalyst Concentration in the ppm Range, *Angew. Chem., Int. Ed.*, 2018, 57, 7898–7902.
- 91 A. Bansal, A. Kumar, P. Kumar, S. Bojja, A. K. Chatterjee, S. S. Ray and S. L. Jain, Visible light-induced surface initiated atom transfer radical polymerization of methyl methacrylate on titania/reduced graphene oxide nanocomposite, *RSC Adv.*, 2015, 5, 21189–21196.
- 92 X. Jiang, M. Xi, L. Bai, W. Wang, L. Yang, H. Chen, Y. Niu, Y. Cui, H. Yang and D. Wei, Surface-initiated PET-ATRP and mussel-inspired chemistry for surface engineering of MWCNTs and application in self-healing nanocomposite hydrogels, *Mater. Sci. Eng., C*, 2020, 109, 110553.
- 93 D. Fan, G. Wang, A. Ma, W. Wang, H. Chen, L. Bai, H. Yang, D. Wei and L. Yang, Surface Engineering of Porous Carbon for Self-Healing Nanocomposite Hydrogels by Mussel-Inspired Chemistry and PET-ATRP, *ACS Appl. Mater. Interfaces*, 2019, 11, 38126–38135.
- 94 E. H. Discekici, C. W. Pester, N. J. Treat, J. Lawrence, K. M. Mattson, B. Narupai, E. P. Toumayan, Y. Luo, A. J. McGrath, P. G. Clark, J. Read de Alaniz and C. J. Hawker, Simple Benchtop Approach to Polymer Brush Nanostructures Using Visible-Light-Mediated Metal-Free Atom Transfer Radical Polymerization, *ACS Macro Lett.*, 2016, 5, 258–262.
- 95 J. Yan, X. Pan, M. Schmitt, Z. Wang, M. R. Bockstaller and K. Matyjaszewski, Enhancing Initiation Efficiency in Metal-Free Surface-Initiated Atom Transfer Radical Polymerization (SI-ATRP), *ACS Macro Lett.*, 2016, 5, 661–665.
- 96 L. Huang, M. Liu, L. Mao, D. Xu, Q. Wan, G. Zeng, Y. Shi, Y. Wen, X. Zhang and Y. Wei, Preparation and controlled drug delivery applications of mesoporous silica polymer nanocomposites through the visible light induced surface-initiated ATRP, *Appl. Surf. Sci.*, 2017, 412, 571–577.
- 97 H.-L. Su, L. Xu, X.-J. Hu, F.-F. Chen, G. Li, Z.-K. Yang, L.-P. Wang and H.-L. Li, Polymer grafted mesoporous SBA-15 material synthesized via metal-free ATRP as pH-sensitive drug carrier for quercetin, *Eur. Polym. J.*, 2021, 148, 110354.
- 98 L. Ma, N. Li, J. Zhu and X. Chen, Visible Light-Induced Metal Free Surface Initiated Atom Transfer Radical Polymerization of Methyl Methacrylate on SBA-15, *Polymers*, 2017, 9, 58.
- 99 S. Jockusch and Y. Yagci, The active role of excited states of phenothiazines in photoinduced metal free atom transfer radical polymerization: singlet or triplet excited states?, *Polym. Chem.*, 2016, 7, 6039–6043.
- 100 X. Xu, J. He, Y. Zeng, C. Yu and F. Zhang, Controllable surface-initiated metal-free atom transfer radical polymerization of methyl methacrylate on mesoporous SBA-15 via reductive quenching, *Eur. Polym. J.*, 2020, 131, 109724.
- 101 X. Xu, Y. Zou, J. He, Y. Zeng, C. Yu and F. Zhang, Insight into the effects of reaction conditions on metal-free surface-initiated atom-transfer radical polymerization of methyl methacrylate from SBA-15, *J. Appl. Phys.*, 2020, 127, 115102.
- 102 J. Meng, J. Li, Y. Zhang and S. Ma, A novel controlled grafting chemistry fully regulated by light for membrane surface hydrophilization and functionalization, *J. Membr. Sci.*, 2014, 455, 405–414.
- 103 F. Kameche, W. Heni, S. Telitel, D. Ge, L. Vidal, F. Dumur, D. Gignes, J. Lalevée, S. Marguet, L. Douillard, C. Fiorini-Deubisshert, R. Bachelot and O. Soppera, Plasmon-triggered living photopolymerization for elaboration of hybrid polymer/metal nanoparticles, *Mater. Today*, 2020, 40, 38–47.
- 104 K. Skrabania, A. Miasnikova, A. M. Bivigou-Koumba, D. Zehm and A. Laschewsky, Examining the UV-vis absorption of RAFT chain transfer agents and their use for polymer analysis, *Polym. Chem.*, 2011, 2, 2074–2083.
- 105 S. Li, G. Han and W. Zhang, Photoregulated reversible addition-fragmentation chain transfer (RAFT) polymerization, *Polym. Chem.*, 2020, 11, 1830–1844.
- 106 T. G. McKenzie, L. P. D. M. Costa, Q. Fu, D. E. Dunstan and G. G. Qiao, Investigation into the photolytic stability of RAFT agents and the implications for photopolymerization reactions, *Polym. Chem.*, 2016, 7, 4246–4253.
- 107 J. Xu, K. Jung, A. Atme, S. Shanmugam and C. Boyer, A robust and versatile photoinduced living polymerization of conjugated and unconjugated monomers and its oxygen tolerance, *J. Am. Chem. Soc.*, 2014, 136, 5508–5519.
- 108 S. Perrier, 50th Anniversary Perspective: RAFT Polymerization—A User Guide, *Macromolecules*, 2017, 50, 7433–7447.
- 109 M. Li, M. Fromel, D. Ranaweera, S. Rocha, C. Boyer and C. W. Pester, SI-PET-RAFT: Surface-Initiated Photoinduced Electron Transfer-Reversible Addition-Fragmentation Chain Transfer Polymerization, *ACS Macro Lett.*, 2019, 8, 374–380.
- 110 T. Otsu, Iniferter concept and living radical polymerization, *J. Polym. Sci., Part A: Polym. Chem.*, 2000, 38, 2121–2136.
- 111 T. Otsu and K. Nayatani, Vinyl polymerization XXVIII. The polymerization of styrene initiated by tetralkyl thiuram disulfides, *Makromol. Chem.*, 1958, 27, 149–156.
- 112 T. Schulte, Entwicklung neuer Alkoxyamine für die Nitroxid-vermittelte kontrollierte lebende radikalische Polymerisation. *Zugl.: Marburg, Univ., Diss.*, Cuvillier, Göttingen, 1st edn, 2004.
- 113 S. Shanmugam, J. Xu and C. Boyer, Light-Regulated Polymerization under Near-Infrared/Far-Red Irradiation Catalyzed by Bacteriochlorophyll a, *Angew. Chem., Int. Ed.*, 2016, 55, 1036–1040.
- 114 S. M. Clouthier, J. Tanaka and W. You, Photomediated RAFT step-growth polymerization with maleimide monomers, *Polym. Chem.*, 2022, 13, 6114–6119.
- 115 A. J. Gormley, J. Yeow, G. Ng, Ó. Conway, C. Boyer and R. Chapman, An Oxygen-Tolerant PET-RAFT Polymerization for Screening Structure-Activity Relationships, *Angew. Chem., Int. Ed.*, 2018, 57, 1557–1562.
- 116 S. V. Wanasinghe, M. Sun, K. Yehl, J. Cuthbert, K. Matyjaszewski and D. Konkolewicz, PET-RAFT Increases Uniformity in Polymer Networks, *ACS Macro Lett.*, 2022, 11, 1156–1161.
- 117 G. Ng, J. Yeow, J. Xu and C. Boyer, Application of oxygen tolerant PET-RAFT to polymerization-induced self-assembly, *Polym. Chem.*, 2017, 8, 2841–2851.



- 118 A. Bagheri, J. Yeow, H. Arandiyani, J. Xu, C. Boyer and M. Lim, Polymerization of a Photocleavable Monomer Using Visible Light, *Macromol. Rapid Commun.*, 2016, **37**, 905–910.
- 119 N. Corrigan, D. Rosli, J. W. J. Jones, J. Xu and C. Boyer, Oxygen Tolerance in Living Radical Polymerization: Investigation of Mechanism and Implementation in Continuous Flow Polymerization, *Macromolecules*, 2016, **49**, 6779–6789.
- 120 S. Shanmugam, J. Xu and C. Boyer, Exploiting Metalloporphyrins for Selective Living Radical Polymerization Tunable over Visible Wavelengths, *J. Am. Chem. Soc.*, 2015, **137**, 9174–9185.
- 121 J. Zhou, C. Hong and C. Pan, The photo-controlled polymerization-induced self-assembly and reorganization process for fabrication of polymeric nanomaterials, *Mater. Chem. Front.*, 2017, **1**, 1200–1206.
- 122 J. Yeow, J. Xu and C. Boyer, Polymerization-Induced Self-Assembly Using Visible Light Mediated Photoinduced Electron Transfer-Reversible Addition-Fragmentation Chain Transfer Polymerization, *ACS Macro Lett.*, 2015, **4**, 984–990.
- 123 A. Bagheri, C. W. A. Bainbridge, K. E. Engel, G. G. Qiao, J. Xu, C. Boyer and J. Jin, Oxygen Tolerant PET-RAFT Facilitated 3D Printing of Polymeric Materials under Visible LEDs, *ACS Appl. Polym. Mater.*, 2020, 782–790.
- 124 A. R. Kuzmyn, L. W. Teunissen, P. Fritz, B. van Lagen, M. M. J. Smulders and H. Zuilhof, Diblock and Random Antifouling Bioactive Polymer Brushes on Gold Surfaces by Visible-Light-Induced Polymerization (SI-PET-RAFT) in Water, *Adv. Mater. Interfaces*, 2022, **9**, 2101784.
- 125 J. Xu, S. Shanmugam, H. T. Duong and C. Boyer, Organophotocatalysts for photoinduced electron transfer-reversible addition-fragmentation chain transfer (PET-RAFT) polymerization, *Polym. Chem.*, 2015, **6**, 5615–5624.
- 126 V. Bellotti and R. Simonutti, New Light in Polymer Science: Photoinduced Reversible Addition-Fragmentation Chain Transfer Polymerization (PET-RAFT) as Innovative Strategy for the Synthesis of Advanced Materials, *Polymers*, 2021, **13**, 1119.
- 127 T. G. McKenzie, E. H. H. Wong, Q. Fu, A. Sulistio, D. E. Dunstan and G. G. Qiao, Controlled Formation of Star Polymer Nanoparticles via Visible Light Photopolymerization, *ACS Macro Lett.*, 2015, **4**, 1012–1016.
- 128 P. Gao, H. Cao, Y. Ding, M. Cai, Z. Cui, X. Lu and Y. Cai, Synthesis of Hydrogen-Bonded Pore-Switchable Cylindrical Vesicles via Visible-Light-Mediated RAFT Room-Temperature Aqueous Dispersion Polymerization, *ACS Macro Lett.*, 2016, **5**, 1327–1331.
- 129 T. Joshi and L. Nebhani, Light-regulated growth of polymer chains from the surface of RAFT agent primed mesoporous silica nanoparticles, *Surf. Interfaces*, 2022, **29**, 101764.
- 130 C. Förster, L. Veith and A. Andrieu-Brunsen, Visible light induced RAFT for asymmetric functionalization of silica mesopores, *RSC Adv.*, 2022, **12**, 27109–27113.
- 131 M. Stanzel, U. Kunz and A. Andrieu-Brunsen, Layer-selective functionalisation in mesoporous double layer via iniferter initiated polymerisation for nanoscale step gradient formation, *Eur. Polym. J.*, 2021, **156**, 110604.
- 132 D. John, M. Stanzel and A. Andrieu-Brunsen, Surface Plasmons and Visible Light Iniferter Initiated Polymerization for Nanolocal Functionalization of Mesoporous Separation Layers, *Adv. Funct. Mater.*, 2021, **31**, 2009732.
- 133 Q. Michaudel, V. Kottisch and B. P. Fors, Kationische Polymerisation: von der Photoinitiation zur Steuerung durch Licht, *Angew. Chem.*, 2017, **129**, 9798–9808.
- 134 J. V. Crivello, The discovery and development of onium salt cationic photoinitiators, *J. Polym. Sci., Part A: Polym. Chem.*, 1999, **37**, 4241–4254.
- 135 G. Yilmaz, S. Beyazit and Y. Yagci, Visible light induced free radical promoted cationic polymerization using thioxanthone derivatives, *J. Polym. Sci., Part A: Polym. Chem.*, 2011, **49**, 1591–1596.
- 136 E. Sari, M. Mitterbauer, R. Liska and Y. Yagci, Visible light induced free radical promoted cationic polymerization using acylsilanes, *Prog. Org. Coat.*, 2019, **132**, 139–143.
- 137 G. Yilmaz, B. Iskin, F. Yilmaz and Y. Yagci, Visible Light-Induced Cationic Polymerization Using Fullerenes, *ACS Macro Lett.*, 2012, **1**, 1212–1215.
- 138 K. Kaya, M. Seba, T. Fujita, S. Yamago and Y. Yagci, Visible light-induced free radical promoted cationic polymerization using organotellurium compounds, *Polym. Chem.*, 2018, **9**, 5639–5643.
- 139 J. V. Crivello, Radical-Promoted Visible Light Photoinitiated Cationic Polymerization of Epoxides, *J. Macromol. Sci., Part A: Pure Appl. Chem.*, 2009, **46**, 474–483.
- 140 J. V. Crivello and M. Sangermano, Visible and long-wavelength photoinitiated cationic polymerization, *J. Polym. Sci., Part A: Polym. Chem.*, 2001, **39**, 343–356.
- 141 K. Kaya, J. Kreutzer and Y. Yagci, A Charge-Transfer Complex of Thioxanthonephenacyl Sulfonium Salt as a Visible-Light Photoinitiator for Free Radical and Cationic Polymerizations, *ChemPhotoChem*, 2019, **3**, 1187–1192.
- 142 J. V. Crivello, A new visible light sensitive photoinitiator system for the cationic polymerization of epoxides, *J. Polym. Sci., Part A: Polym. Chem.*, 2009, **47**, 866–875.
- 143 S. Dadashi-Silab, H. Bildirir, R. Dawson, A. Thomas and Y. Yagci, Microporous Thioxanthone Polymers as Heterogeneous Photoinitiators for Visible Light Induced Free Radical and Cationic Polymerizations, *Macromolecules*, 2014, **47**, 4607–4614.
- 144 M. U. Kahveci, G. Acik and Y. Yagci, Synthesis of Block Copolymers by Combination of Atom Transfer Radical Polymerization and Visible Light-Induced Free Radical Promoted Cationic Polymerization, *Macromol. Rapid Commun.*, 2012, **33**, 309–313.
- 145 C. Aydogan, M. Ciftci, A. M. Asiri and Y. Yagci, Visible light induced one-pot synthesis of amphiphilic hyperbranched copolymers, *Polymer*, 2018, **158**, 90–95.
- 146 X. Xiong, W. Liu, Y. Luan, J. Du, Z. Wu and H. Chen, A Versatile, Fast, and Efficient Method of Visible-Light-Induced Surface Grafting Polymerization, *Langmuir*, 2014, **30**, 5474–5480.
- 147 X. Xiong, Z. Wu, J. Pan, L. Xue, Y. Xu and H. Chen, A facile approach to modify poly(dimethylsiloxane) surfaces via visible light-induced grafting polymerization, *J. Mater. Chem. B*, 2015, **3**, 629–634.
- 148 M. Ciftci, P. Batat, A. L. Demirel, G. Xu, M. Buchmeiser and Y. Yagci, Visible Light-Induced Grafting from Polyolefins, *Macromolecules*, 2013, **46**, 6395–6401.
- 149 M. Ciftci, S. Kork, G. Xu, M. R. Buchmeiser and Y. Yagci, Polyethylene-g-poly(cyclohexene oxide) by Mechanistic Transformation from ROMP to Visible Light-Induced Free Radical Promoted Cationic Polymerization, *Macromolecules*, 2015, **48**, 1658–1663.
- 150 K. Koumura, K. Satoh and M. Kamigaito, Mn₂(CO)₁₀-induced controlled/living radical copolymerization of vinyl acetate and methyl acrylate: Spontaneous formation of block copolymers consisting of gradient and homopolymer segments, *J. Polym. Sci., Part A: Polym. Chem.*, 2009, **47**, 1343–1353.
- 151 M. Ciftci, M. A. Tasdelen and Y. Yagci, Macromolecular design and application using Mn₂(CO)₁₀-based visible light photoinitiating systems, *Polym. Int.*, 2016, **65**, 1001–1014.
- 152 Q. Liu, L. Liu, Y. Ma, C. Zhao and W. Yang, Visible light-induced controlled radical polymerization of methacrylates with perfluoroalkyl iodide as the initiator in conjugation with a photoredox catalyst *fac*-[Ir(ppy)₃], *J. Polym. Sci., Part A: Polym. Chem.*, 2014, **52**, 3283–3291.
- 153 B. P. Fors and C. J. Hawker, Control of a Living Radical Polymerization of Methacrylates by Light, *Angew. Chem., Int. Ed.*, 2012, **51**, 8850–8853.
- 154 J. Lalevée, H. Mokbel and J.-P. Fouassier, Recent Developments of Versatile Photoinitiating Systems for Cationic Ring Opening Polymerization Operating at Any Wavelengths and under Low Light Intensity Sources, *Molecules*, 2015, **20**, 7201–7221.
- 155 A. E. Goetz and A. J. Boydston, Metal-Free Preparation of Linear and Cross-Linked Polydicyclopentadiene, *J. Am. Chem. Soc.*, 2015, **137**, 7572–7575.
- 156 K. A. Ogawa, A. E. Goetz and A. J. Boydston, Metal-Free Ring-Opening Metathesis Polymerization, *J. Am. Chem. Soc.*, 2015, **137**, 1400–1403.
- 157 P. Lu, N. M. Alrashdi and A. J. Boydston, Bidirectional metal-free ROMP from difunctional organic initiators, *J. Polym. Sci., Part A: Polym. Chem.*, 2017, **55**, 2977–2982.
- 158 C. Theunissen, M. A. Ashley and T. Rovic, Visible-Light-Controlled Ruthenium-Catalyzed Olefin Metathesis, *J. Am. Chem. Soc.*, 2019, **141**, 6791–6796.
- 159 O. Eivgi, A. Vaisman, N. B. Nechmad, M. Baranov and N. G. Lemcoff, Latent Ruthenium Benzylidene Phosphite Complexes for Visible-Light-Induced Olefin Metathesis, *ACS Catal.*, 2020, **10**, 2033–2038.



- 160 K. A. Ogawa, A. E. Goetz and A. J. Boydston, Developments in Externally Regulated Ring-Opening Metathesis Polymerization, *Synlett*, 2016, 203–214.
- 161 D. P. Mohite, Z. J. Larimore, H. Lu, J. T. Mang, C. Sotiriou-Leventis and N. Leventis, Monolithic Hierarchical Fractal Assemblies of Silica Nanoparticles Cross-Linked with Polynorbornene via ROMP: A Structure–Property Correlation from Molecular to Bulk through Nano, *Chem. Mater.*, 2012, **24**, 3434–3448.
- 162 M. Ochs, R. Mohammadi, N. Vogel and A. Andrieu-Brunsen, Wetting-Controlled Localized Placement of Surface Functionalities within Nanopores, *Small*, 2020, **16**, e1906463.
- 163 F. Krohm, J. Kind, R. Savka, M. Alcaraz Janßen, D. Herold, H. Plenio, C. M. Thiele and A. Andrieu-Brunsen, Photochromic spirocyan- and spirooxazine-homopolymers in mesoporous thin films by surface initiated ROMP, *J. Mater. Chem. C*, 2016, **4**, 4067–4076.
- 164 J. Elbert, J. Mersini, N. Vilbrandt, C. Lederle, M. Kraska, M. Gallei, B. Stühn, H. Plenio and M. Rehahn, Reversible Activity Modulation of Surface-Attached Grubbs Second Generation Type Catalysts Using Redox-Responsive Polymers, *Macromolecules*, 2013, **46**, 4255–4267.
- 165 F. Ziegler, H. Kraus, M. J. Benedikter, D. Wang, J. R. Bruckner, M. Nowakowski, K. Weißer, H. Solodenko, G. Schmitz, M. Bauer, N. Hansen and M. R. Buchmeiser, Confinement Effects for Efficient Macrocyclization Reactions with Supported Cationic Molybdenum Imido Alkylidene N-Heterocyclic Carbene Complexes, *ACS Catal.*, 2021, **11**, 11570–11578.
- 166 F. Ziegler, T. Roeder, M. Pyschik, C. P. Haas, D. Wang, U. Tallarek and M. R. Buchmeiser, Olefin Ring-closing Metathesis under Spatial Confinement and Continuous Flow, *ChemCatChem*, 2021, **13**, 2234–2241.
- 167 F. Ziegler, J. Teske, I. Elser, M. Dyballa, W. Frey, H. Kraus, N. Hansen, J. Rybka, U. Tallarek and M. R. Buchmeiser, Olefin Metathesis in Confined Geometries: A Biomimetic Approach toward Selective Macrocyclization, *J. Am. Chem. Soc.*, 2019, **141**, 19014–19022.

